

# Results for plateA36\_0.98 : Crack Propagation Plate Thru Center Flaw

Author: edit this in file makereport2

Affiliation:

Thu Aug 29 12:39:14 EDT 2013

Simulation input data:

**B**= 10.0 mm

**W**= 70.0 mm

**a<sub>0</sub>**= 1.5 mm

#MATERIAL= merged\_a36\_fitted.html


#TYPE= plate\_thru\_flaw

\_\_\_\_\_ #ACTIVATE\_fw= 1



Crack Propagation Results:

( #plateThruFlaw.f vers. 3.07 )


- No. of Reversals= 3286972 revs. or 1643486 cycles
- Final \_\_\_\_\_ **a** = 0.182E+02 mm
- No. of History Reps.= 234784 reps. + 10 revs.

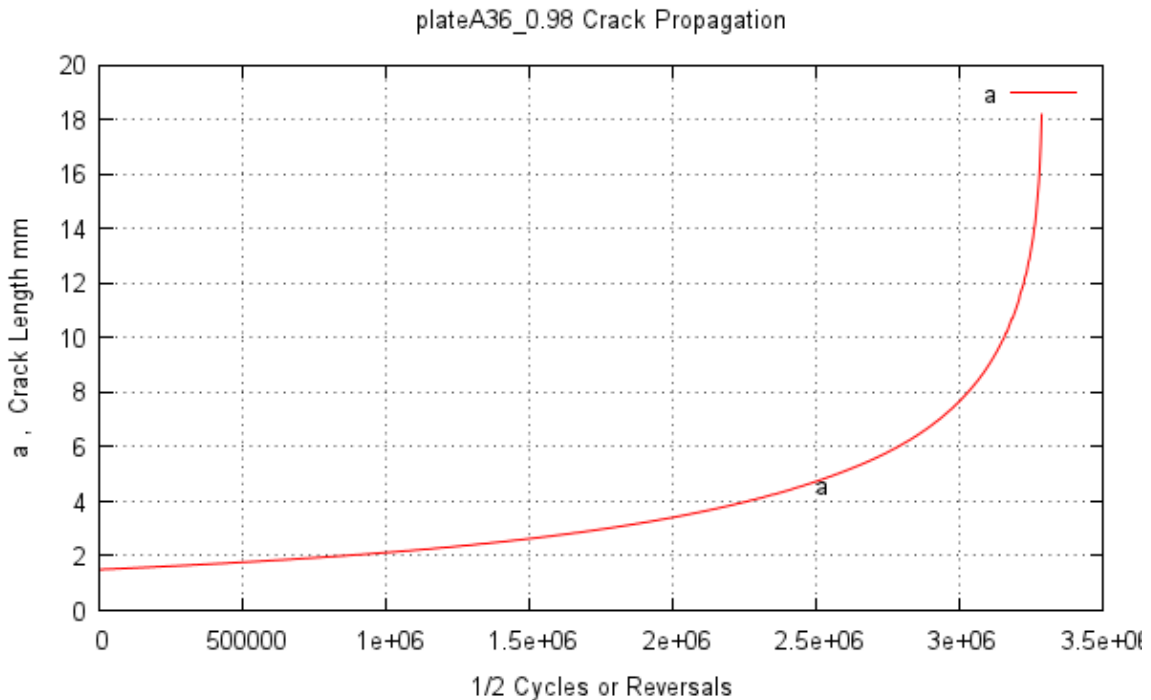


# Results for plateA36\_0.98 : Crack Propagation Plate Thru Center Flaw

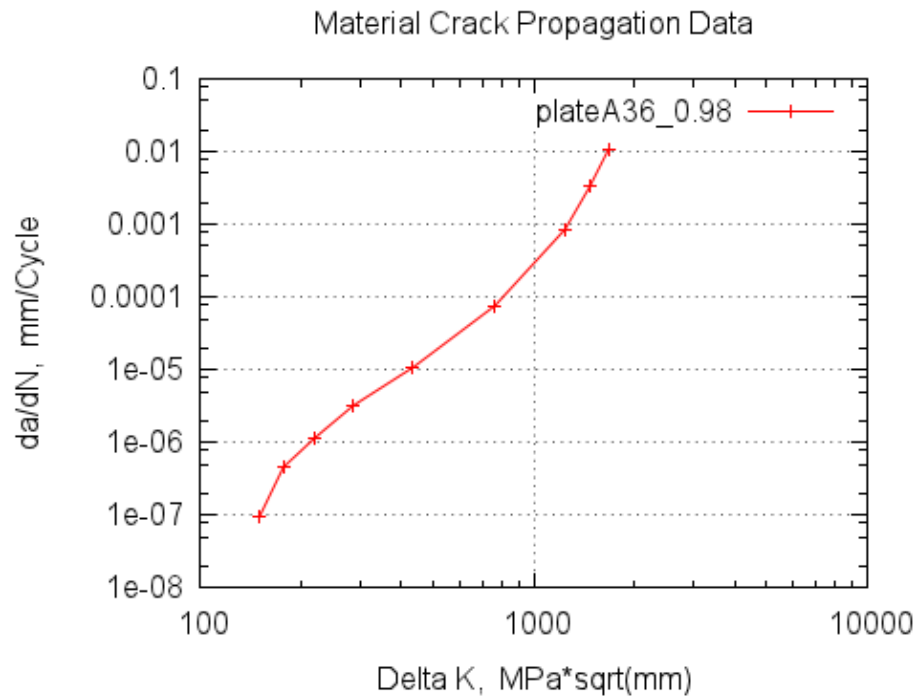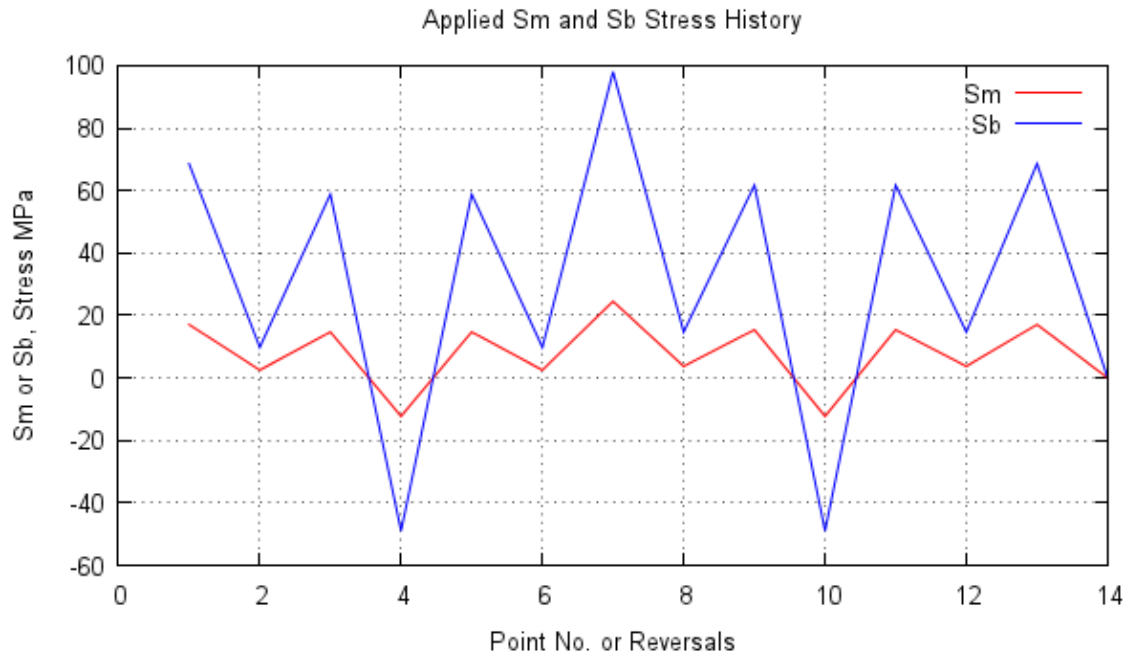

Results for plateA36\_0.98 : Crack Propagation Plate Thru Center Flaw

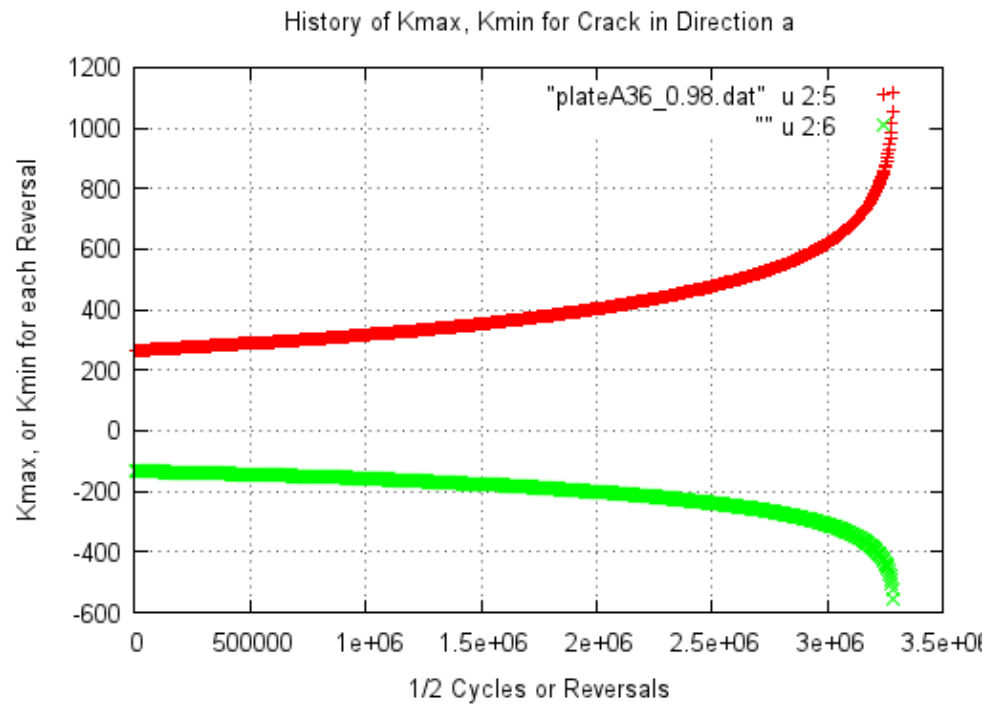

Results for plateA36\_0.98 : Crack Propagation Plate Thru Center Flaw

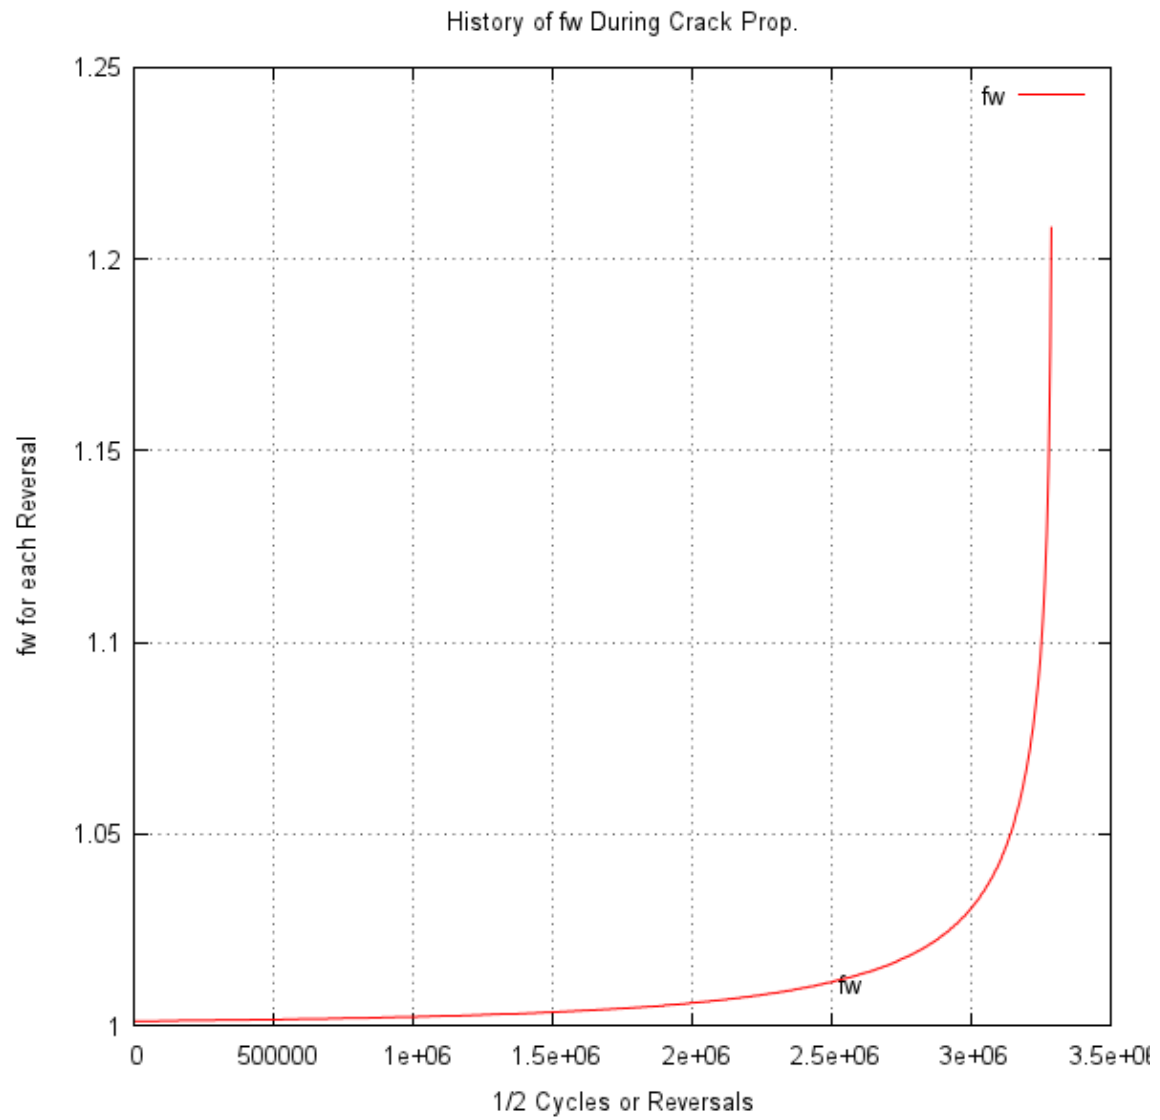


# FAD Results for plateA36\_0.98

#TensileFile= a36\_Mattos\_mono\_engrSS\_FLAT.txt

#PmEOL= 70. #PbEOL= 100.

#Kmat= 1675.

#PinJoint= 0

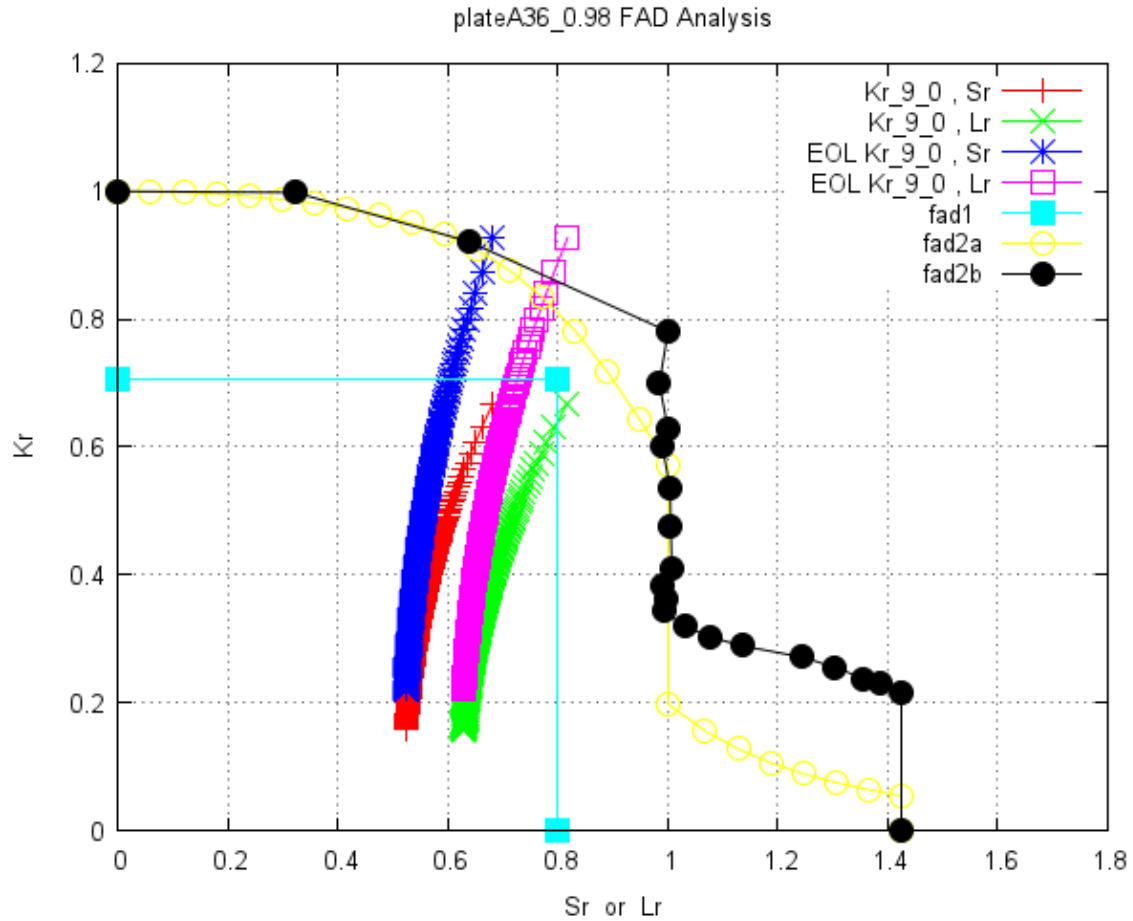

## Crack Initiation Life Results for plateA36\_0.98 (Assume $K_t= 1.8$ for welds)

Files Used:


- Stress History (Sb+Sm)
- Rainflow File
- Material File

| Loop | Smax  | Smin   | N   | Sigmax | Sigmin | Delta | Epsmax  | Epsmin  | DeltaEps | %Eps | %SWaT | %Sts | %Morr |
|------|-------|--------|-----|--------|--------|-------|---------|---------|----------|------|-------|------|-------|
| 1    | 219.6 | -110.3 | 1.0 | 199.   | -108.  | 307.  | 0.00119 | -.00055 | 0.00174  | 0.0  | 0.0   | 0.0  | 0.0   |
| 2    | 152.3 | -110.3 | 1.0 | 136.   | -108.  | 244.  | 0.00084 | -.00055 | 0.00139  | 0.0  | 0.0   | 0.0  | 0.0   |
| 3    | 152.3 | -0.1   | 1.0 | 136.   | -6.    | 142.  | 0.00084 | 0.00003 | 0.00080  | 0.0  | 0.0   | 0.0  | 0.0   |
| 4    | 131.2 | 20.9   | 2.0 | 117.   | 14.    | 103.  | 0.00072 | 0.00014 | 0.00058  | 0.0  | 0.0   | 0.0  | 0.0   |
| 5    | 136.4 | 31.5   | 2.0 | 121.   | 24.    | 98.   | 0.00075 | 0.00020 | 0.00055  | 0.0  | 0.0   | 0.0  | 0.0   |


Predicted History Repetitions to Initiation:

| StrainLife_Reps | SWaT_Life_Reps | StressLife_Reps | Morrow_Reps | Goodman_Reps (Reps= Repetitions) |
|-----------------|----------------|-----------------|-------------|----------------------------------|
| Infinity        | Infinity       | Infinity        | Infinity    | Infinity                         |

### Local Stress and Strain Response:

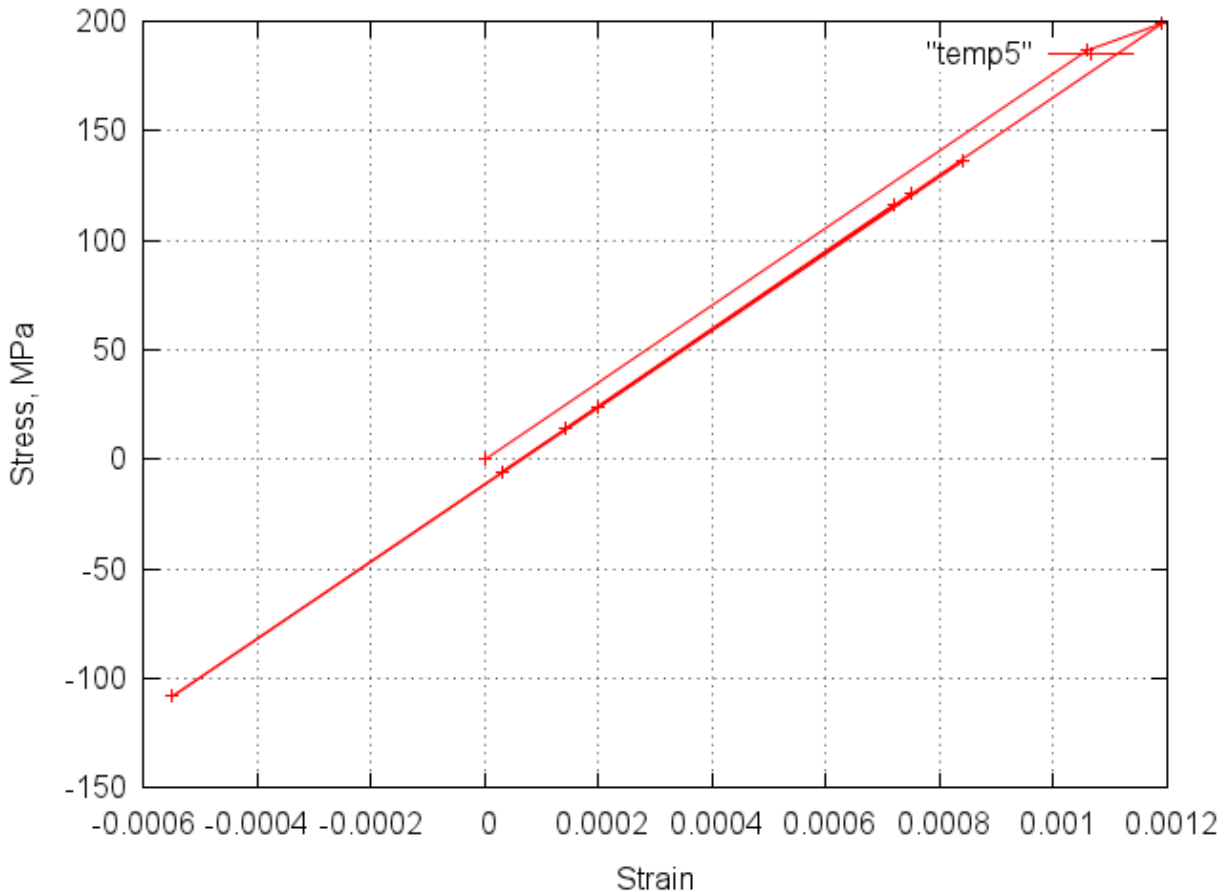

## Cumulative Cycle Plot of History and Damage:

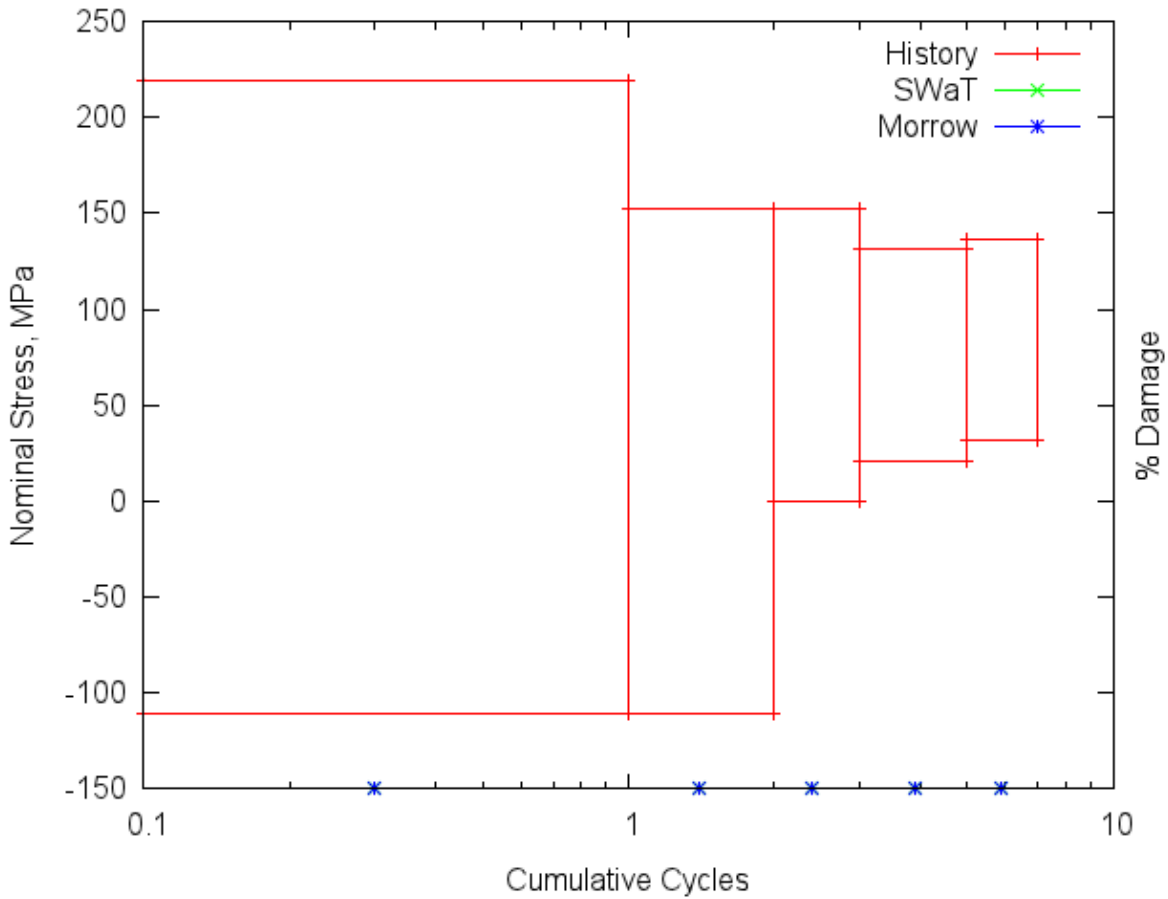

(Rectangles are Rainflow Cycle Sets: Sorted by Range: largest on Left)

## Appendix 1: Print of "pdprop.env" Simulation Control file

```
# This file contains the starting filenames, variables etc
# for the Crack Propagation programs. It should be edited by the
# user before each simulation run. It can also be generated from web
# page at: to be determined
#
#TYPE= plate_thru_flaw      #with or without weld using ACTIVATES:
#       According to BS7910 M=Mm=Mb=1.0 and no welds.
#ACTIVATE_MmMb= 0 # ignored
#ACTIVATE_MkmMkb= 0 # ignored
#ACTIVATE_fw= 1 # Deactivate = 0
#
#       #Other #TYPE= options:
#       # plate_surface_flaw
#       # plate_long_surface_flaw
#       # plate_embedded_flaw
#       # plate_edge_flaw
#
#       # pipe_inside_flaw
#       # pipe_full_inside_flaw
#       # pipe_full_outside_flaw
#
#       # rod_surface_flaw
```

## Results for plateA36\_0.98 : Crack Propagation Plate Thru Center Flaw

```
#                               # rod_full_outside_flaw

#                               # These problem types are used to pull in the
#                               # appropriate Fw, Mm, Mb, files etc.

# The factors described in this section may be ignored if not applicable to
# the particular problem type described above.
# (All dimensions in mm)
#B= 10.0   # plate (or pipe wall) thickness
#W= 70.0   # plate width
#ri=  0.    # Internal diameter if pipe problem. Ignored if not pipe
#azero= 1.5 # initial crack half length
#czero= 0.0 # initial 1/2 crack width at surface (not used for plate_tru_flaw)
#L=  0.    # Weld Feature width. Ignored if ACTIVATE_MkmMkb= 0 (above)

#HISTORYFILE= load1.txt   # historyFileName
#                               # Adjustments to load file variables:
#                               # Note that the MEANADD (below) is added AFTER the MAGFACTOR is applied.
#MAGFACTOR_m= 1.0        # Multiply factor on membrane load. Result should be MPa
#MAGFACTOR_b= 1.0        # Multiply factor on bending load term. Result should be MPa
#MEANADD_m=  0.0         # Mean shift in MPa added to membrane stress.
#MEANADD_b=  0.0         # Mean shift in MPa added to bending stress.

#MAXREPS=  1000000       # Max no. history repeats in simulation.
#                               # One repetition or application of the load history is
#                               # also called a "block" of cycles.
#
#
#MATERIAL= merged_a36_fitted.html #File name of material fitted data
#                               # This file is used to define the cyclic
#                               # stress-strain curve, and the Neuber Product curve.
#
#DADN= table                # Can be "table" or "Paris"
#DADN_PARIS= 0.0 0.0 0.0 0.0 none # Kth a m Kc units (ignored if #DADN= table )
#DADN_TABLE= a36+1015.dadn # da/dN digitized da/dN curve for material,
#                               # including the threshold, and KIc.
#                               # If a threshold exists, put in a vertical line
#                               # (with two identical X-axis points).
#                               # If the threshold needs to be "turned off" then
#                               # do NOT put in a vertical line at low da/dN.
#                               # (Ignored when #DADN= PARIS )
#
#FAD Stuff:
#TensileFile= a36_Mattos_mono_engrSS_FLAT.txt #enter "none" if no FAD
#PmEOL= 70. #Set these so that Pm+Pb= 0.82*Syield for default.
#PbEOL= 100.
#Kmat= 1675.
#PinJoint= 0 #Set = 1 if struture is pinJointed (for bending)
#
#BLOCKSKIP= 1.0 percent # At the end of each block check if the previous
#                               # two blocks of cycles had similar damage (crack
#                               # extension) within this percentage. If TRUE then
#                               # simply skip the simulation of the next block,
#                               # but just add the expected damage. Continue by
#                               # simulating the block after the skip.
#                               # A value of 0.0 will disallow skipping blocks.
#SAVELEVEL= 0 #Amount of output saved to disk:
#                               # 3=lots 2=medium 1=minimal
#                               # 0= save #crk= data into binary direct access file only
#                               # No #crk= data will be written into the text logfile.
#                               # Use for large output files with lots of cycles.
```



## Appendix 2: Print of da/dn vs DeltaK Table in file plateA36\_0.98

| Delta_K       | da/dN         |               |                |               |               |   |
|---------------|---------------|---------------|----------------|---------------|---------------|---|
| 0.1502160E+03 | 0.9620540E-07 | 0.2176716E+01 | -0.7016800E+01 | 0.0000000E+00 | 0.0000000E+00 | 1 |
| 0.1769830E+03 | 0.4562300E-06 | 0.2247931E+01 | -0.6340816E+01 | 0.7121539E-01 | 0.6759844E+00 | 2 |
| 0.2202350E+03 | 0.1160170E-05 | 0.2342886E+01 | -0.5935478E+01 | 0.9495497E-01 | 0.4053378E+00 | 3 |
| 0.2874840E+03 | 0.3224090E-05 | 0.2458614E+01 | -0.5491593E+01 | 0.1157272E+00 | 0.4438853E+00 | 4 |
| 0.4331670E+03 | 0.1069760E-04 | 0.2636655E+01 | -0.4970714E+01 | 0.1780417E+00 | 0.5208793E+00 | 5 |
| 0.7637410E+03 | 0.7556810E-04 | 0.2882946E+01 | -0.4121662E+01 | 0.2462907E+00 | 0.8490520E+00 | 6 |
| 0.1240590E+04 | 0.8520410E-03 | 0.3093628E+01 | -0.3069540E+01 | 0.2106822E+00 | 0.1052122E+01 | 7 |
| 0.1471680E+04 | 0.3307300E-02 | 0.3167813E+01 | -0.2480526E+01 | 0.7418513E-01 | 0.5890131E+00 | 8 |
| 0.1675690E+04 | 0.1074680E-01 | 0.3224194E+01 | -0.1968721E+01 | 0.5638027E-01 | 0.5118057E+00 | 9 |

## Appendix 3: Print of Stress-Strain-Init.Life file: "matfile"

#SAE Standard Fatigue Data File format

##

Pick one: #FDE\_plot #FDE\_fit ##

```
#
#Copyright (C) 2012 F.D.E. Committee
#This data file is free software - you can redistribute it and/or
#modify it under the terms of the GNU General Public License as
#published by the Free Software Foundation; either version 2 of the
#license, or (at your option) any later version.
#This data file is distributed in the hope that it will be useful,
#but WITHOUT ANY WARRANTY - without even the implied warranty of
#MERCHANTABILITY or FITNESS FOR A PARTICULAR PURPOSE. See the
#GNU General Public License for more details.
#You should have received a copy of the GNU General Public License
#along with this program - if not, write to the Free Software
#Foundation, Inc., 59 Temple Place - Suite 330, Boston, MA 02111-1307, USA
#Try also their web site: http://www.gnu.org/copyleft/gpl.html
#
# NOTE: Fitted Data !!
# A36 Steel Merged Data Sets from Refs. 1 and 2:
# Ref.1: P.Dindinger report to Fat.Des.+Eval. Comm. Apr.2012
# Ref.2: G.A.Miller and H.S.Reemsnyder, "Strain-Cycle Fatigue of Sheet and
# Plate Steels I: Test Method Development and Data Presentation,"
# SAE Paper 830175, Detroit MI, Feb28-Mar.4, 1983
#
# NOTE that original test data ends at 2Nf = 1.3million.
#
#FileType= strain_life
#DataType= fitted
#TIMEcol= 0
#NAME= ASTM-A36
#NAME= Structural
#NAME= Steel
#Stress_units= ksi
#Strain_units= strain
#Sy= 38.4 0.2pc offset, 265 mpa
#Su= 69. ksi from Miller/Reemsnyder = 475 mpa
#eu= 0 #strain at Su not reported
```

## Results for plateA36\_0.98 : Crack Propagation Plate Thru Center Flaw

```

#E= 29528. ksi = 203600 mpa
#FractureStrain= 0 not reported
#FractureStress= 0. not reported
#monotonic_K= 0 not reported
#monotonic_n= 0 not reported
#BHN= 138.
#%RA= 0. % not reported
#
#saedigcurve_v2.2.f starts.
# NOTE!! The Following Points are FITTED DATA:#NOTE!! Fitted Stress computed using Experm.
# Total Strain      2Nf  Stress Mean      Plastic Strain      Initial
#      Amp              Amp      Stress              Amp              Elastic Mod.
  0.88485             1      115.3             0.      0.88095          29528. #Fitted_point
  0.00914            5000     52.1             0.      0.00737          29528. #Fitted_point
  0.00665           10000     48.8             0.      0.00499          29528. #Fitted_point
  0.00493           20000     45.7             0.      0.00338          29528. #Fitted_point
  0.00344           50000     42.0             0.      0.00202          29528. #Fitted_point
  0.00270          100000     39.3             0.      0.00136          29528. #Fitted_point
  0.00217          200000     36.8             0.      0.00092          29528. #Fitted_point
  0.00169          500000     33.8             0.      0.00055          29528. #Fitted_point
  0.00144         1000000     31.6             0.      0.00037          29528. #Fitted_point
#Original test data ends at 2Nf = 1.3million.
#Points below are extrapolation:
  0.00125          2000000     29.6             0.      0.00025          29528. #Fitted_point
  0.00106          5000000     27.1             0.      0.00014          29528. #Fitted_point
#
#

```