

SAE 4140 Quenched and Tempered Steel Iteration #69

Fatigue Behavior, Monotonic Properties and Microstructural Data

Prepared by:

A.A. Rteil
and
T.H. Topper

Department of Civil Engineering
University of Waterloo
Waterloo, Ontario Canada

Prepared for:
The AISI Bar Steel Applications Group

May 2005 (revised)



**American
Iron and Steel
Institute**

American Iron and Steel Institute
2000 Town Center, Suite 320
Southfield, Michigan 48075
tel: 248-945-4777
fax: 248-352-1740
www.autosteel.org

TABLE OF CONTENTS

SUMMARY	3
INTRODUCTION.....	4
EXPERIMENTAL PROCEDURE.....	4
Specimen Preparation.....	4
Test Equipment and Procedure	4
RESULTS.....	5
A) Microstructure Data	5
B) Strain-Life Data	6
C) Cyclic Stress-Strain Curves.....	6
D) Mechanical Properties.....	7
REFERENCES	7

SUMMARY

The required microstructure data, mechanical properties, cyclic stress-strain data and strain-controlled fatigue data for 4140 Quenched and Tempered steel (Iteration # 69) have been obtained. The material was provided by the American Iron and Steel Institute (AISI) in the form of 2.25" round bars. These bars were machined into smooth axial fatigue specimens. Two monotonic tensile tests were performed to measure the yield strength, the tensile strength and the reduction of area. Twenty-two specimens were fatigue tested in laboratory air at room temperature to establish a strain-life curve.

INTRODUCTION

This report presents the results of tensile and fatigue tests performed on a group of 4140 Quenched and Tempered steel samples. The material was provided by the American Iron and Steel Institute.

The objectives of this investigation were to obtain the microstructural data, mechanical properties, cyclic stress-strain data and strain-life fatigue data requested by the AISI bar group.

EXPERIMENTAL PROCEDURE

Specimen Preparation

The material for the study was received in the form of 2.25" round bars. Smooth cylindrical fatigue specimens, shown in Figure 1, were machined from the metal bars. The gauge sections of the fatigue specimens were mechanically polished in the loading direction using 240, 400, 500, and 600 emery paper. After polishing, a thin band of M-coat D acrylic coating was applied along the central gauge section. The purpose of the M-coat D application was to prevent scratching of the smooth surface by the knife-edges of the strain extensometer, thus reducing the incidence of knife-edge failures. In total, 22 fatigue data points were generated.

Test Equipment and Procedure

Two monotonic tension tests were performed to determine the yield strength, the tensile strength, the percent elongation and the percent reduction of area. Hardness tests were performed on the surface of three fatigue specimens using a Rockwell C scale. The hardness measurements were repeated three times for each specimen and the average value was recorded.

All fatigue tests were carried out in a laboratory environment at approximately 25 °C using an MTS servo-controlled closed loop electrohydraulic testing machine. A process control computer, controlled by FLEX software [1] was used to output constant strain and stress amplitudes in the form of a sinusoidal wave.

Axial, constant amplitude, fully reversed ($R=-1$) strain-controlled fatigue tests were performed on smooth specimens. The stress-strain limits for a given cycle of each specimen were recorded at logarithmic intervals throughout the test via a peak reading voltmeter. Failure of a specimen was defined as a 50 percent drop in tensile peak load from the peak load observed at one half the expected specimen life. For fatigue lives greater than 100,000 reversals, the specimens were tested in stress-control once the stress-strain loops had stabilized. For the stress-

controlled tests, failure was defined as the separation of the smooth specimen into two pieces. For strain-controlled tests the loading frequency varied from 0.03 Hz to 3 Hz while in stress-controlled tests the frequency used was up to 60 Hz.

The first reversal of each fatigue test was recorded on a x-y plotter, allowing the elastic modulus (E) and the monotonic yield strength to be determined.

RESULTS

A) Microstructure Data

Figure 2 presents the martensite microstructure of the 4140 Quenched and Tempered steel (It #69). A Type D series inclusion severity level of 1.0 was obtained based on ASTM E45 (Method A). Inclusions of types A, B and C were not observed. Figure 3 shows the inclusions observed in the 4140 Quenched and Tempered steel (It #69). The inclusion area was measured using a JAVA image analysis system.

B) Strain-Life Data

The fatigue test data for 4140 Quenched and Tempered steel (It #69) obtained in this investigation are given in Table 1. The stress amplitude corresponding to each strain amplitude was calculated from the peak load amplitude at the specimen half-life.

A fatigue strain life curve for the 4140 Quenched and Tempered steel is shown in Figure 4, and is described by the following equation:

$$\frac{\Delta\varepsilon}{2} = \frac{\sigma'_f}{E} (2N_f)^b + \varepsilon'_f (2N_f)^c$$

where

$\frac{\Delta\varepsilon}{2}$	= True total strain amplitude
$2N_f$	= Number of reversals to failure
σ'_f	= Fatigue strength coefficient
b	= Fatigue strength exponent
ε'_f	= Fatigue ductility coefficient
c	= Fatigue ductility exponent

where $\sigma'_f = 1423.7$ MPa, $b = -0.053$, $\varepsilon'_f = 2.649$ and $c = -0.842$. These values of the strain-life parameters were determined from fatigue testing over the range: $0.003 < \frac{\Delta\varepsilon}{2} < 0.01$.

C) Cyclic Stress-Strain Curves

Stabilized and half-life stress data obtained from strain-life fatigue tests were used to obtain the companion cyclic stress-strain curve shown in Figure 5. The cyclic stress-strain curve is described by the following equation:

$$\varepsilon = \frac{\sigma}{E} + \left(\frac{\sigma}{K'} \right)^{\frac{1}{n'}}$$

where ε = True total strain amplitude
 σ = Cyclically stable true stress amplitude
 K' = Cyclic strength coefficient
 n' = Cyclic strain hardening exponent

where $K' = 1109.9$ MPa and $n' = 0.0359$.

The true monotonic and true cyclic stress-strain curves plotted together are given in Figure 6.

D) Mechanical Properties

The engineering monotonic tensile stress-strain curves are given in Figure 7. The monotonic and cyclic properties are included in Appendix 1. The Hardness of the 4140 Quenched and Tempered steel (It #69) was taken as the average of three randomly chosen fatigue specimens and is given in Appendix 1. The individual hardness measurements are also given in Table 1.

REFERENCES

- [1] Pompetzki, M.A., Saper, R.A., and Topper, T.H., "Software for High Frequency Control of Variable Amplitude Fatigue Tests," Canadian Metallurgical Quarterly, Vol. 25, No. 2, pp. 181-194, 198.
- [2] J. A. Bannantine, J. J. Comer, and J. L. Handrock (1990), In :Fundamentals of Metal Fatigue Analysis, Prentice Hall, London.



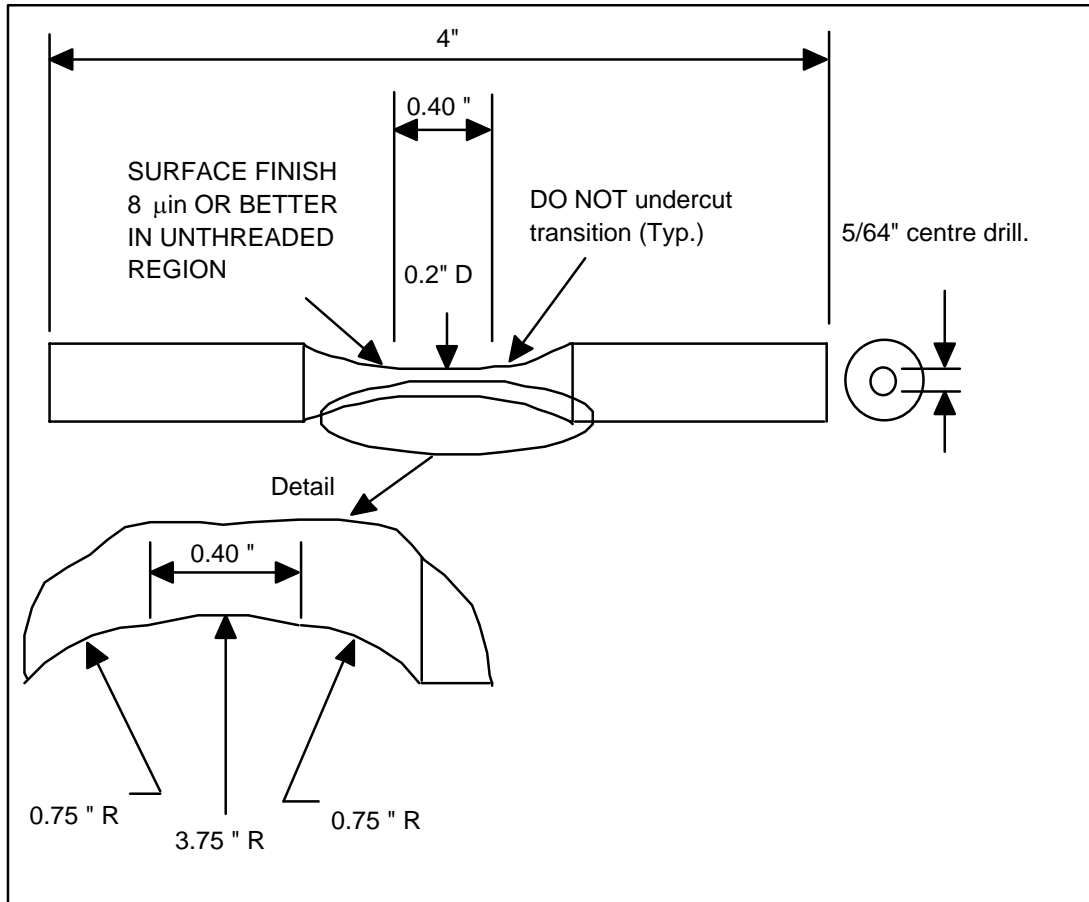


Figure 1 Smooth cylindrical fatigue specimen

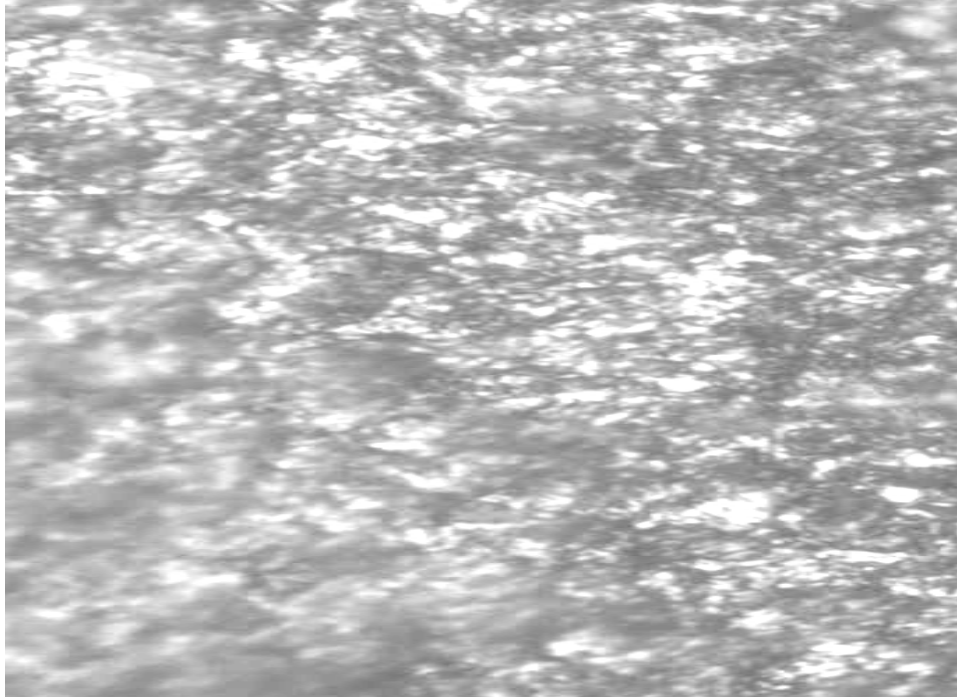

(a) Longitudinal Direction

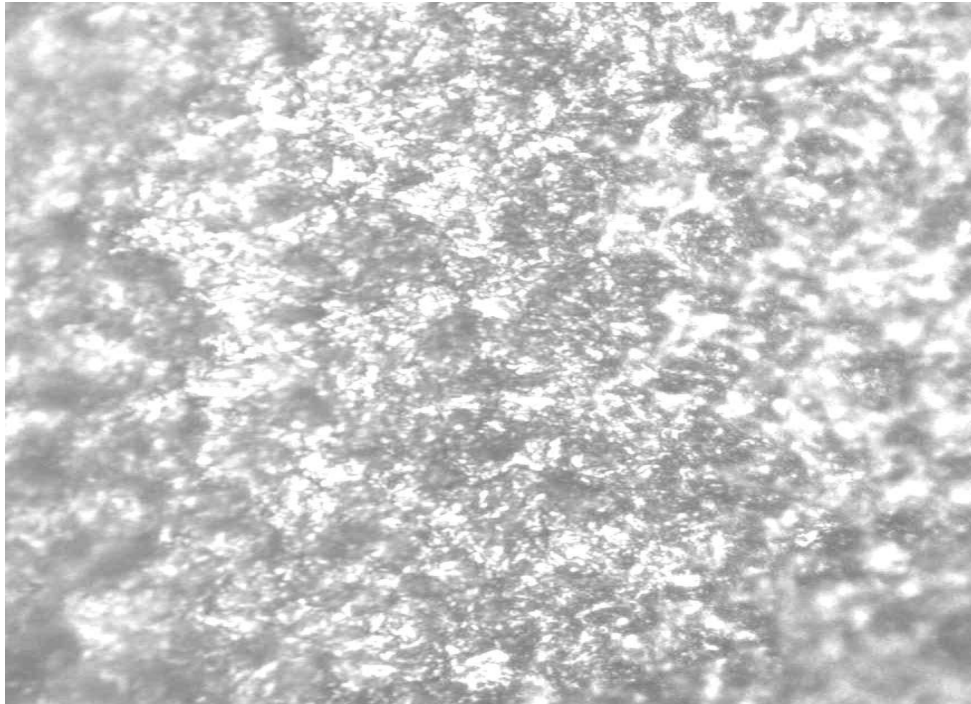

(b) Transverse Direction

Figure 2 Photomicrographs of 4140 Quenched and Tempered steel (X500)

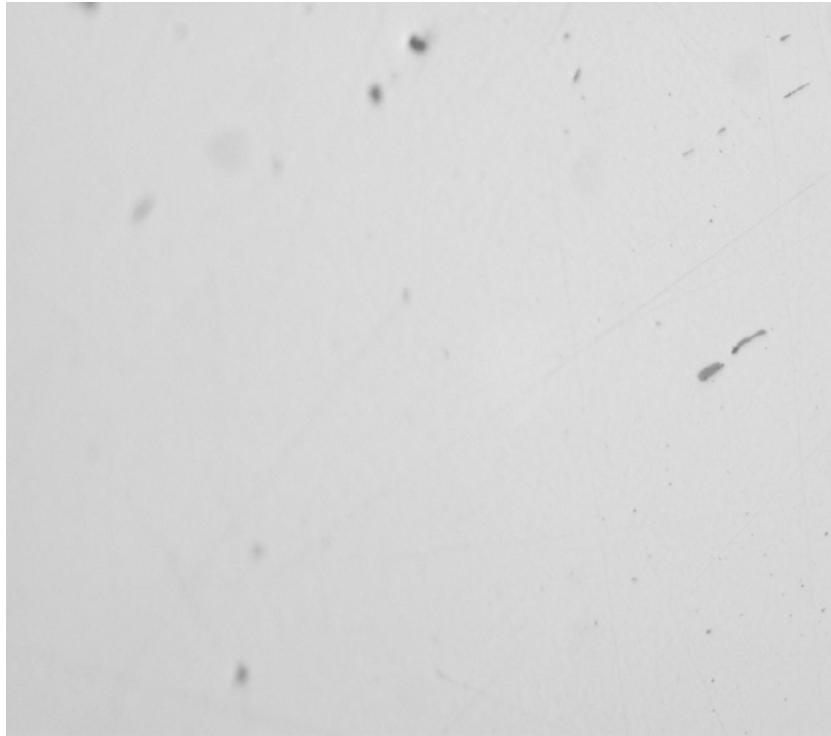


Figure 3 Inclusions photomicrograph of 4140 Quenched and Tempered steel (X100)

4140 Quenched and Tempered (Iteration 69)

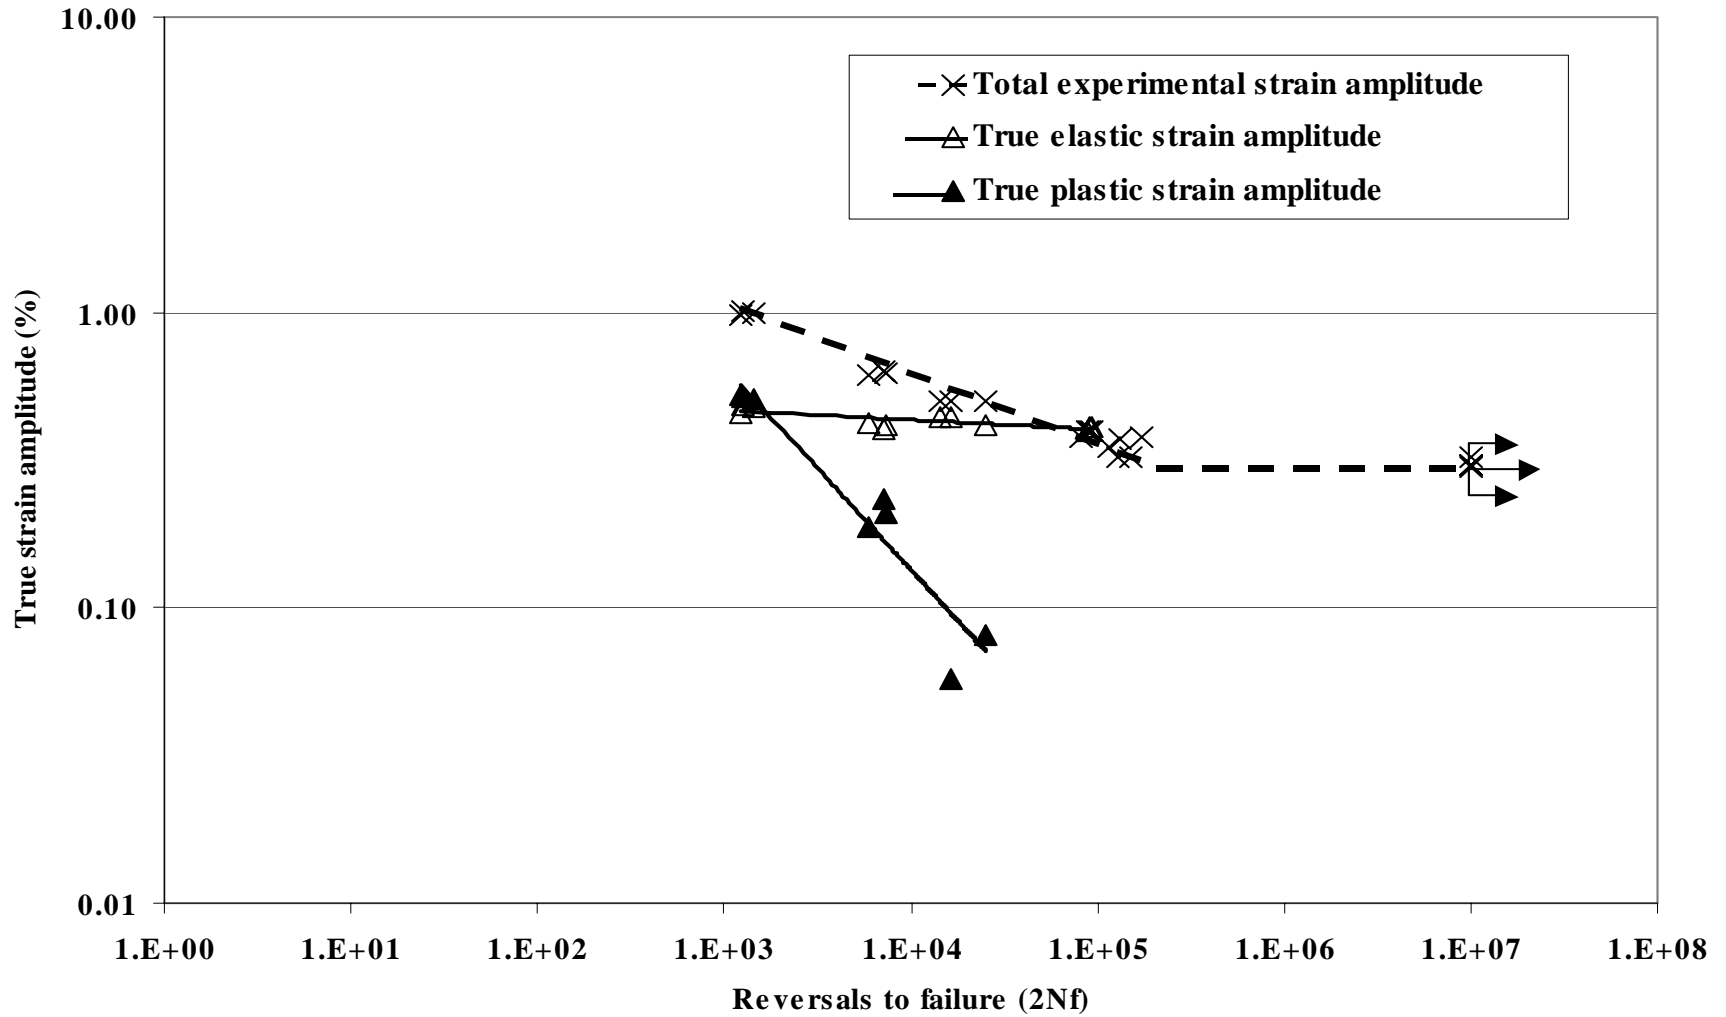


Figure 4. Constant amplitude fully reversed strain-life curve for 4140 Quenched and Tempered steel (Iteration 69).

4140 Quenched and Tempered (Iteration 69)

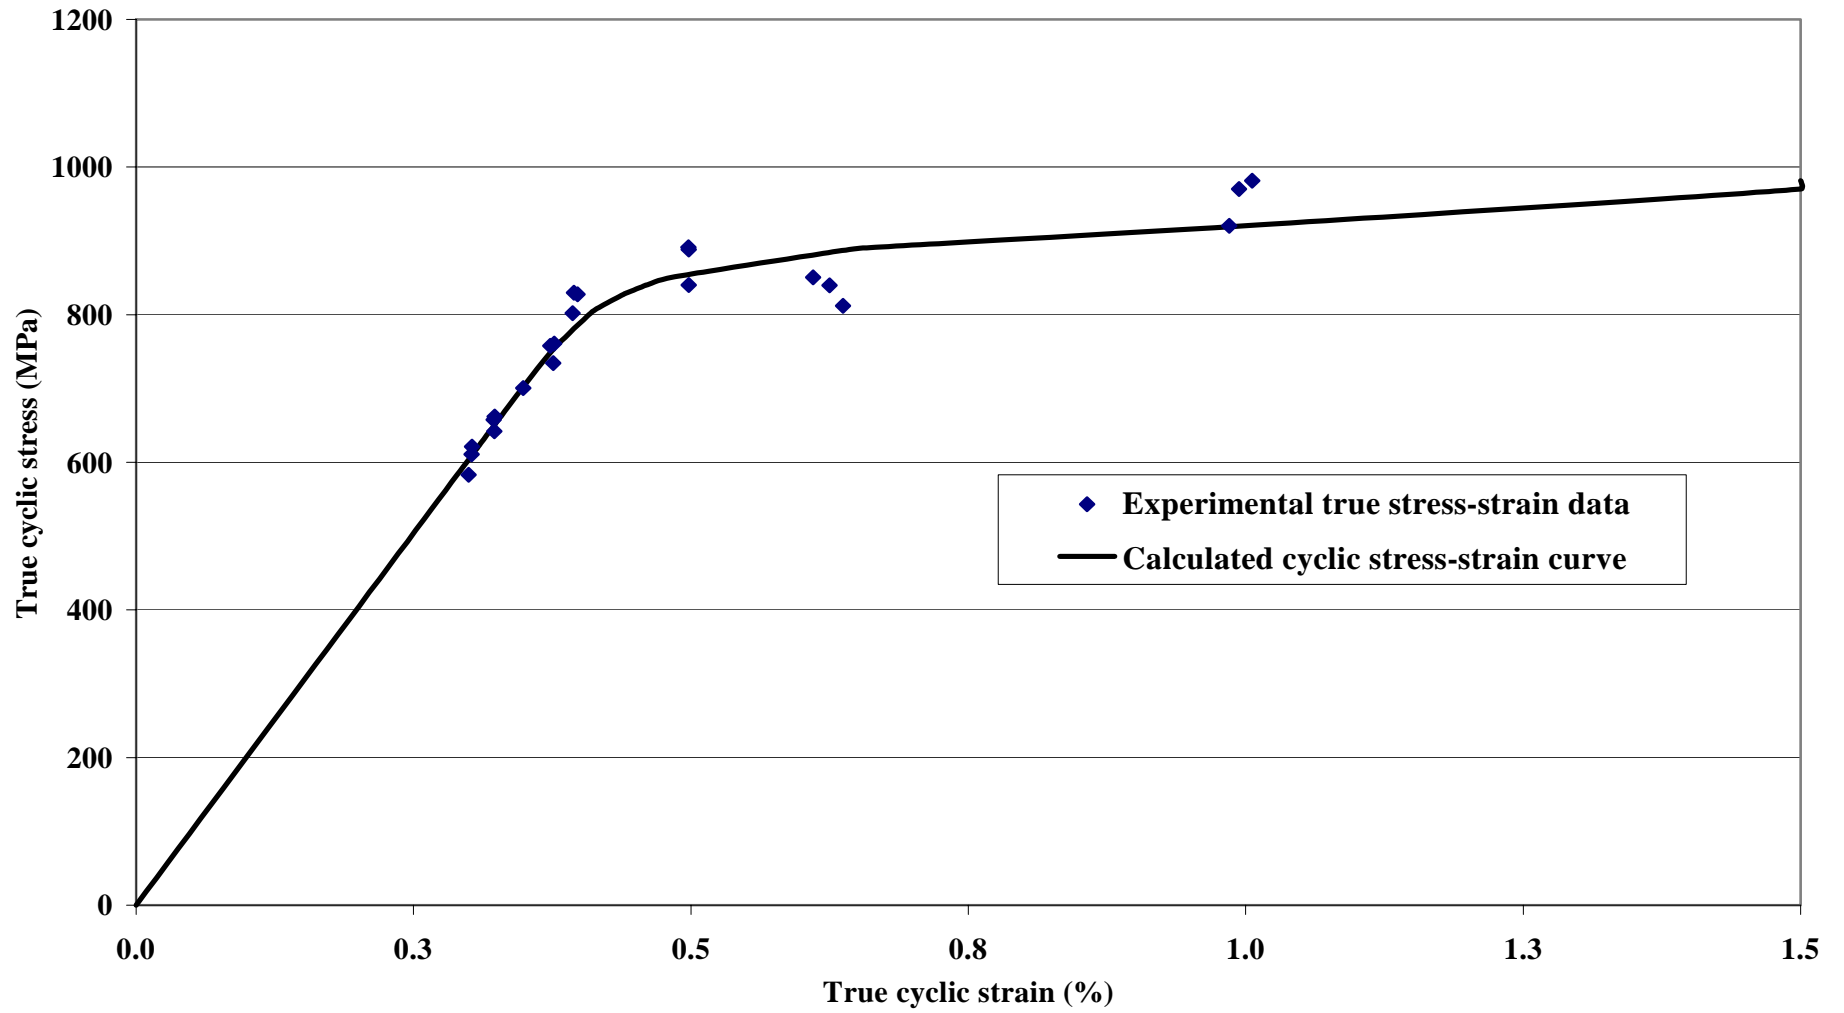


Figure 5. Cyclic stress-strain curve for 4140 Quenched and Tempered steel (Iteration 69).

4140 Quenched and Tempered (Iteration 69)

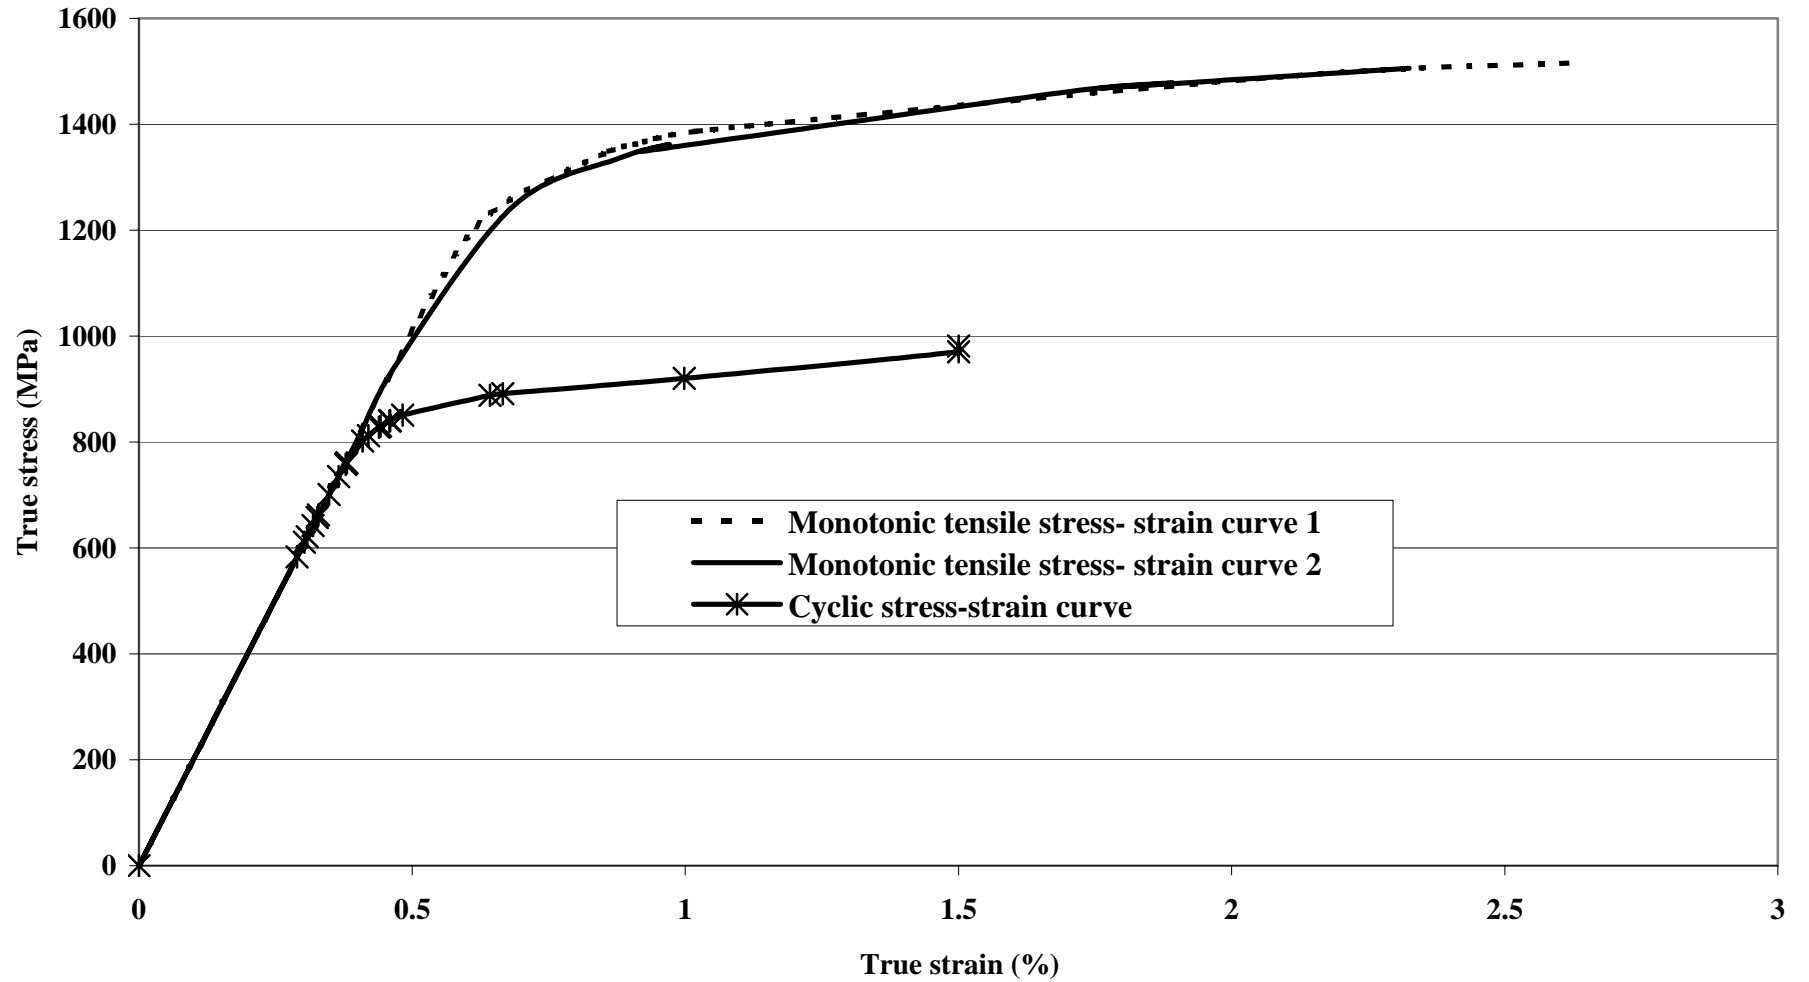


Figure 6. Monotonic and Cyclic stress-strain curves for 4140 Quenched and Tempered steel (Iteration 69).

4140 Quenched and Tempered (Iteration 69)

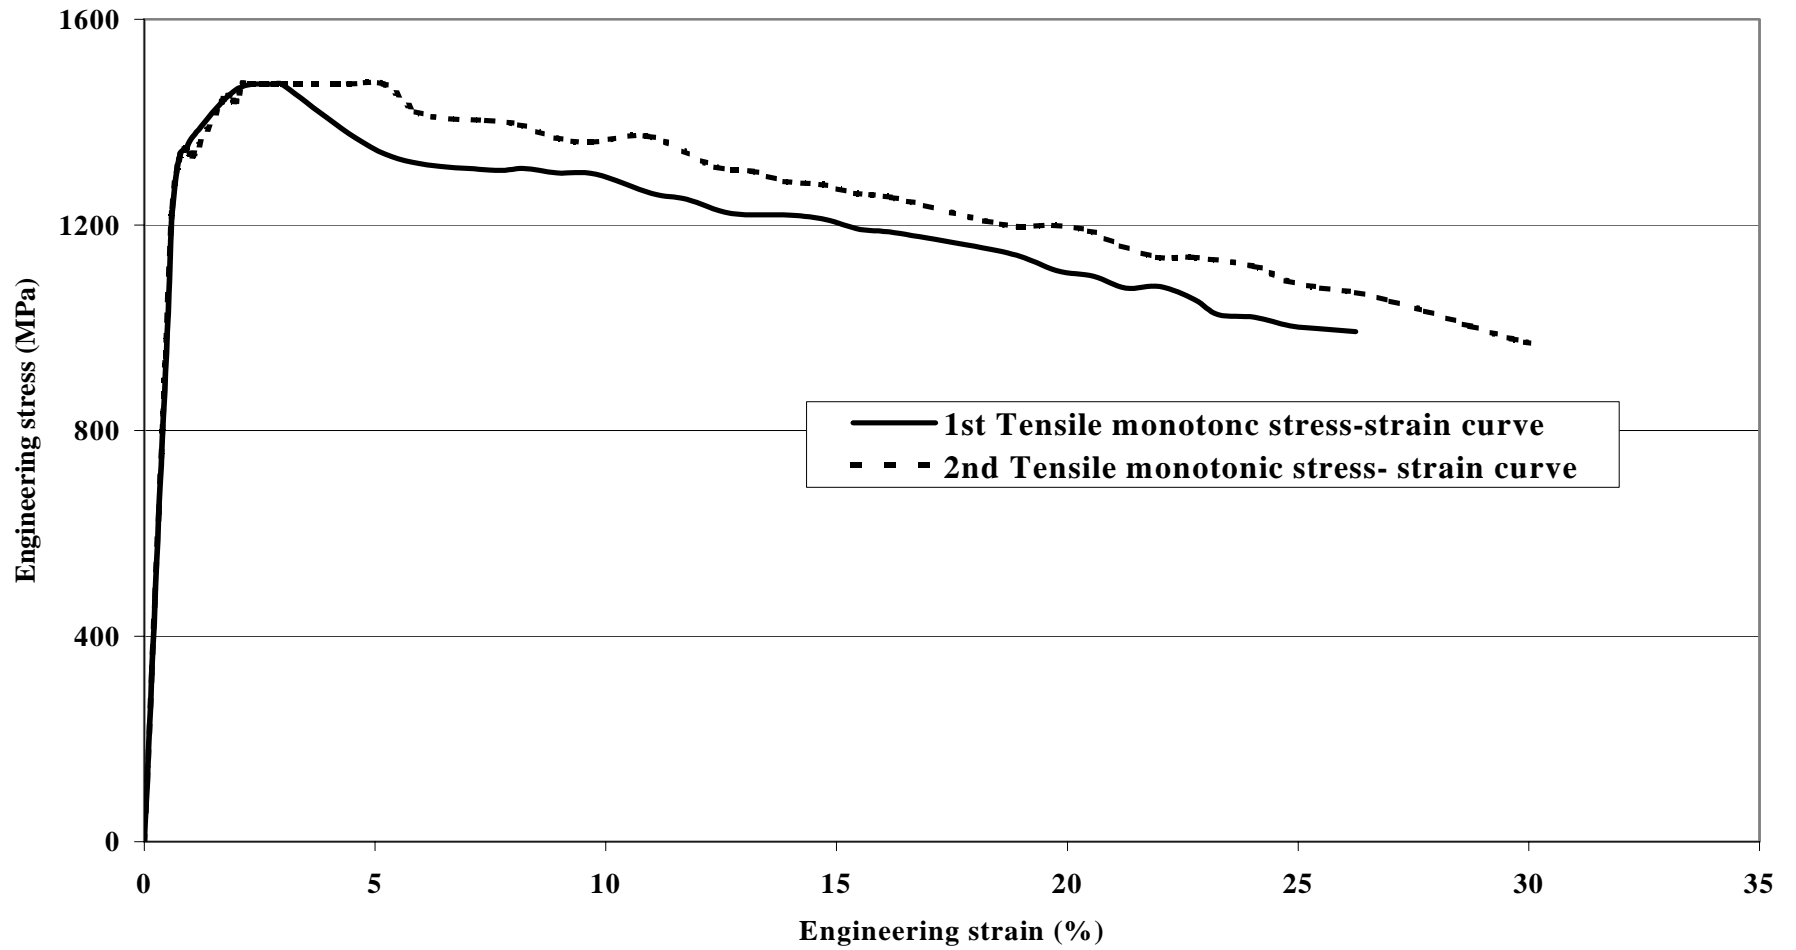


Figure 7. Tensile monotonic stress-strain curves for two 4140 Quenched and Tempered steel specimens (Iteration 69).

Table 1 Fatigue Data for the 4140 Quenched and Tempered steel (Iteration 69)

Sp#	Total Strain Amplitude(%)	Stress Amplitude (MPa)	Plastic Strain Amplitude(%)	Elastic Strain Amplitude(%)	(50% load drop) Fatigue Life (Reversals, 2Nf)	Hardness (Rockwell C)	Monotonic Young's Modulus (GPa)
1	0.994	970.3	0.512	0.482	1444	--	201.7
2	1.006	981.5	0.519	0.487	1244	--	200.9
3	0.985	920.3	0.528	0.457	1224	--	--
4	0.610	850.6	0.188	0.422	5940	--	204.4
5	0.625	839.6	0.208	0.417	7360	40.7	196.3
6	0.637	812.1	0.234	0.403	7220	--	--
7	0.498	888.2	0.057	0.441	16520	--	204.3
8	0.498	891.5	0.055	0.443	14220	--	206.8
9	0.498	840.2	0.081	0.417	25284	--	186.1
10	0.395	830.0	0.000	0.395	90700	--	204.8
11	0.393	801.9	0.000	0.393	88620	40.7	201.7
12	0.398	827.8	0.000	0.398	93460	--	--
13	0.377	761.0	0.000	0.377	172620	--	204.3
14	0.373	757.6	0.000	0.373	131492	--	--
15	0.376	734.5	0.000	0.376	81004	--	--
16	0.349	700.7	0.000	0.349	116244	--	203.1
17*	0.322	657.6	0.000	0.322	10000000	--	203.4
18	0.323	642.1	0.000	0.323	149140	--	198.6
19	0.323	662.0	0.000	0.323	128000	--	206.5
20*	0.300	583.1	0.000	0.300	10000000	--	196.3
21*	0.303	621.1	0.000	0.303	10000000	39.3	205.7
22*	0.302	610.6	0.000	0.302	10000000	--	203.4

*Run out

Appendix 1

Monotonic Properties for 4140 Quenched and Tempered steel (Iteration 69).

Average Elastic Modulus, E	=	201.4 GPa
Yield Strength	=	1341 MPa
Ultimate tensile Strength	=	1474.2 MPa
% Elongation	=	28.2 %
% Reduction of Area	=	52.5 %
True fracture strain, $Ln (A_i / A_f)$	=	74.5 %
True fracture stress, $\sigma_f = \frac{P_f}{A_f}$	=	2063.6 MPa
Bridgman correction, $\sigma_f = \frac{P_f}{A_f} / \left(1 + \frac{4R}{D_f}\right) Ln \left(1 + \frac{D_f}{4R}\right)$		= 1786.2 MPa
Monotonic tensile strength coefficient, K	=	1894.6 MPa
Monotonic tensile strain hardening exponent, n	=	0.056
Hardness, Rockwell C (HRC)	=	40

Cyclic Properties for 4140 Quenched and Tempered steel (Iteration 69).

Cyclic Yield Strength, (0.2% offset) = $K'(0.002)^{n'}$	=	888 MPa
Cyclic strength coefficient, K'	=	1109.9 MPa
Cyclic strain hardening exponent, n'	=	0.0359
Fatigue Strength Coefficient, σ'_f	=	1423.7 MPa
Fatigue Strength Exponent, b	=	-0.053
Fatigue Ductility Coefficient, ϵ'_f	=	2.649
Fatigue Ductility Exponent, c	=	-0.842

P _f :	Load at fracture.
A _i and A _f :	Specimen cross-section area before and after fracture.
R:	Specimen neck radius.
D _f	Specimen diameter at fracture.