



Fatigue Behavior and Monotonic Properties

For

AISI 4320 Steel

Iterations 124 &148

T.H. Topper, M. EL-Zeghayar and M. Yu

Department of Civil and Environmental Engineering

University of Waterloo

Waterloo, Ontario, Canada N2L 3G1

Prepared for:

The SMDI Bar Steel Applications Group

January, 2011



Steel Market Development Institute
2000 Town Center, Suite 320
Southfield, Michigan 48075
tel: 248-945-4777
fax: 248-352-1740
www.autosteel.org

Table of Contents

Summary.....3

Introduction.....4

Experimental Procedure.....4

Specimen Preparation 4

Test Equipment and Procedure..... 4

Results.....5

Chemical Composition..... 5

Monotonic Test..... 5

Cyclic Stress-Strain Curves 6

Constant Amplitude Fatigue Data..... 6

Overload Fatigue Data 7

Microstructure.....8

References.....9

Summary

The required mechanical fatigue properties, cyclic stress-strain data, strain-controlled fatigue data and overload fatigue data for AISI 4320 Steel have been obtained. The material was provided by the American Iron and Steel Institute (AISI) in the form of metal bars. These bars were machined into smooth axial fatigue specimens. The Rockwell C hardness (RC) was determined as the average of nine measurements. Constant-amplitude tests as well as overload fatigue tests were conducted in laboratory air at room temperature to establish the cyclic stress-strain curve, strain-life curve as well as the effective strain-life curve.

Introduction

This report presents the results of tensile and fatigue tests performed on a group of 4320 Steel specimens (Iteration 124 and 148). The material was provided by the American Iron and Steel Institute. The objective of this investigation is to obtain the mechanical fatigue properties, cyclic stress-strain data, strain-life fatigue data, and overload data of this material.

Experimental Procedure

Specimen Preparation

The material for this study was received in the form of round bars. Smooth cylindrical fatigue specimens, shown in Figure 1, were machined from the cylindrical metal bars. Before testing, the specimens had a final polish in the loading direction in the gauge sections using 240, 400, 500, and 600 emery paper and a thin band of M-coat D acrylic coating was applied along the central gauge section. The purpose of the M-coat D application was to prevent scratching of the smooth surface by the knife-edges of the strain extensometer, thus reducing the incidence of knife-edge failures.

Test Equipment and Procedure

Two monotonic tension tests were performed to determine the yield strength, the tensile strength, the percent of elongation and the percent reduction of area. Hardness tests were performed on the surface of three fatigue specimens using a “Rockwell C” scale. The hardness measurements were repeated three times for each specimen and the average value was recorded. All fatigue tests

were carried out in a laboratory environment at approximately 25°C using an MTS servo-controlled closed loop electro hydraulic testing machine.

A process control computer, controlled by FLEX software [1] was used to output constant strain amplitudes for constant strain amplitude tests and stress amplitudes for the overload tests.

Axial, constant strain amplitude, fully reversed ($R=-1$) strain-controlled fatigue tests were performed on smooth specimens. The stress-strain limits for each specimen were recorded at logarithmic intervals throughout the test via a peak reading voltmeter. Failure of a specimen was defined as a 50 percent drop in the tensile peak load from the peak load observed at one half the expected specimen life. The loading frequency varied from 0.05 Hz to 3 Hz. For fatigue lives greater than 100,000 reversals (once the stress-strain loops had stabilized) in constant amplitude tests and in periodic overload tests, the specimens were tested in load control. For the load-controlled tests, failure was defined as the separation of the smooth specimen into two pieces. The test frequencies used in this case were between 50 and 80 Hz.

Results

Chemical Composition

The chemical composition as provided by MacSteel is shown in Table 1.

Monotonic Tension Test

The engineering monotonic tensile stress-strain curve is given in Figure 2. The monotonic properties are given in Table 2. The Hardness of the 4320 Steel was taken as the average of the values obtained from three randomly chosen fatigue specimens and is given in Table 2

Cyclic Stress-Strain Curves

Stabilized stress data obtained from strain-life fatigue tests were used to construct the companion specimen cyclic stress-strain curve shown in Figure 3. The true monotonic and true cyclic stress-strain curves are plotted together in Figure 4. The cyclic stress-strain curve is described by the following equation:

$$\varepsilon = \frac{\sigma}{E_c} + \left(\frac{\sigma}{K'} \right)^{\frac{1}{n}} \quad \text{(Eq. 1)}$$

Where ε is the true total strain amplitude, σ is the cyclically stable true stress amplitude, E_c is the cyclic modulus of elasticity obtained from a best fit of the above equation to the test data and is given in Table 2, K' is the cyclic strength coefficient, and n' is the strain hardening exponent

Constant Amplitude Fatigue Data

Constant amplitude fatigue test data obtained in this investigation are given in Table 3. The stress amplitude corresponding to the peak strain amplitude was calculated from the peak load amplitude at one half of the specimen's life. A constant amplitude fatigue life curve for 4320 Steel is given in Figure 5 and is described by the following equations:

$$\frac{\Delta \varepsilon_e}{2} = \frac{\sigma_f^1}{E} (2N_f)^b \quad \text{(Eq. 2)}$$

$$\frac{\Delta \varepsilon_p}{2} = \varepsilon_f^1 (2N)^c \quad \text{(Eq. 3)}$$

$$\text{Since } \Delta \varepsilon = \Delta \varepsilon_e + \Delta \varepsilon_p \quad \text{(Eq. 4)}$$

$$\frac{\Delta\varepsilon}{2} = \frac{\sigma'_f}{E} (2N_f)^b + \varepsilon'_f (2N_f)^c \quad (\text{Eq. 5})$$

Where;

$\frac{\Delta\varepsilon}{2}$ is the total strain amplitude,

$\frac{\Delta\varepsilon_e}{2}$ is the elastic strain amplitude $\left(\frac{\Delta\varepsilon_e}{2} = \frac{\Delta\varepsilon_{measured}}{2} - \frac{\Delta\varepsilon_p}{2} \right)$,

$\frac{\Delta\varepsilon_p}{2}$ is the plastic strain amplitude $\left(\frac{\Delta\varepsilon_p}{2} = \frac{\Delta\varepsilon_{measured}}{2} - \frac{\Delta\sigma_{measured}}{2E} \right)$,

$2N_f$ is the number of reversals to failure,

σ'_f is the fatigue strength coefficient,

b is the fatigue strength exponent,

ε'_f is the fatigue ductility coefficient,

c is the fatigue ductility exponent.

The values of the strain-life parameters were determined from a best fit of Equations 2 and 3 and are given in Table 2.

Overload Fatigue Test Data

Previous work at the University of Waterloo introduced an effective strain-life curve for use in fatigue damage calculations due to overloads [2]. This effective strain-life curve is derived from periodic overload tests consisting of two blocks of load cycles repeated. The first block consists of a single R=-1 overload (tensile and compressive overload peaks) cycle, and this is followed by a block of smaller load cycles that have the same tensile peak stress as the overload cycle. The minimum of the small cycles varies from test to test, and similarly the number of small cycles

between the overload cycles is varied depending upon the expected life. These two blocks are then repeated until the specimen fails. The aim is to have the large cycle (overload cycle) occur frequently enough that the crack opening stress remains below the minimum stress of the smaller cycles and crack growth during the application of the small cycles is free of crack closure. The overload cycle amplitude used in this testing for iteration 148 was set equal to the fully reversed constant-amplitude stress level that would give a fatigue life of 10,000 cycles. The reason for this choice was to achieve a large reduction in crack opening stress without allotting an undue fraction of the total damage to the large cycles. The number of small cycles in the second block was chosen so that they did 80 to 90% of the damage to the specimen and that they were free from closure. The damage due to the overloads was removed using Miner's rule [3] and the equivalent failure life of the small cycles in each test was calculated. The overload fatigue data for iteration 148 are given in Table 4. The equivalent strain-life fatigue curve is shown together with constant amplitude fatigue life curve in Figure 6.

Microstructure:

Microstructure was analyzed by Chrysler lab, as shown in Figure 7 and 8.

References

- [1] M. Pompetzki, R. Saper, T. Topper, Software for rig frequency control of variable amplitude fatigue tests, *Canadian Metallurgical Quarterly* 25 (2) (1987) 181-194
- [2] T. Topper, T. Lam, Effective strain-fatigue life data for variable amplitude loading, *International Journal of Fatigue* 19 (1) (1997) 137-143
- [3] I. Stephens, *Metal Fatigue in Engineering*, Second edition, John Wiley & Sons, 2001

Note:

Some specimen IDs, a digital number with a letter “B”, such as 12B, it means this specimen (12) was tested at low strain amplitude without failure, then it was tested at high strain amplitude (12B).

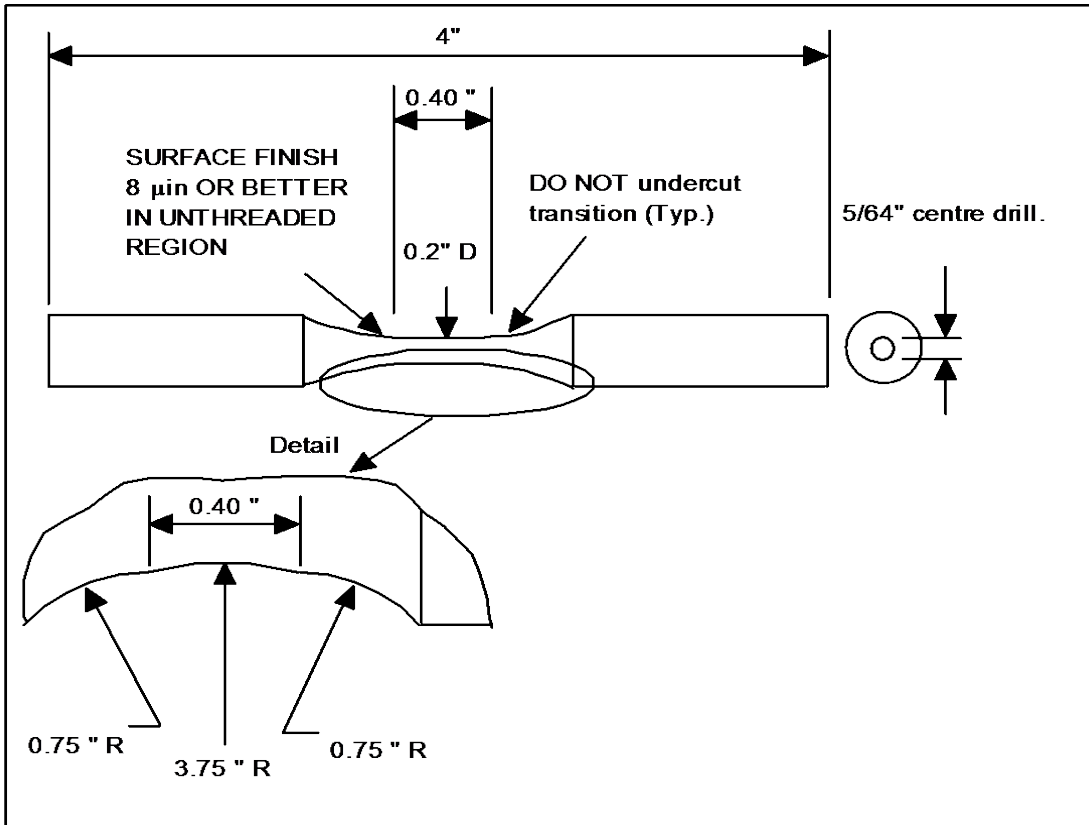


Figure 1: Uni-axial smooth cylindrical fatigue specimen

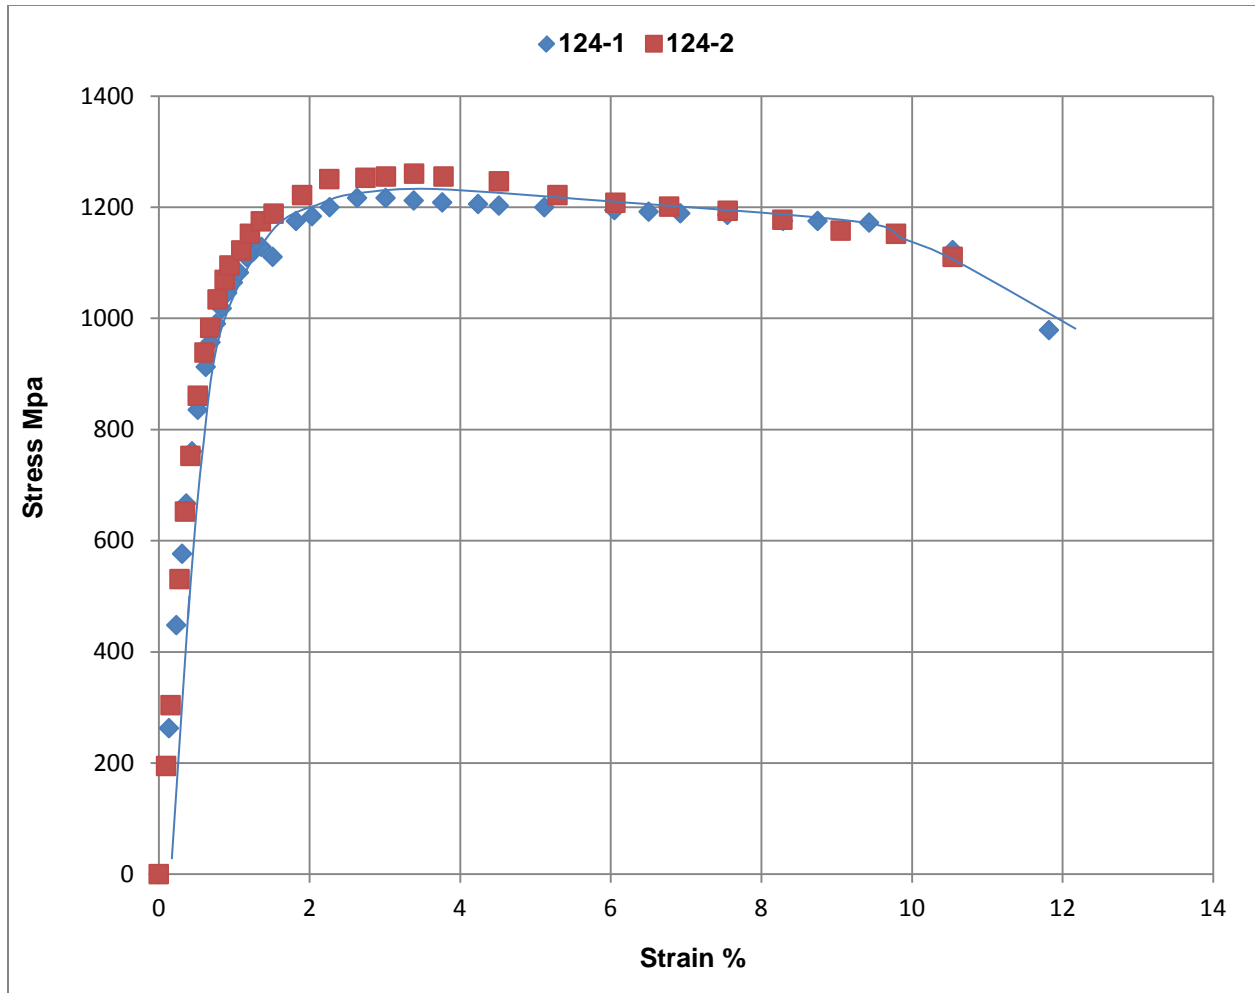


Figure 2: Monotonic engineering stress-strain curves for AISI 4320 (IT 124)

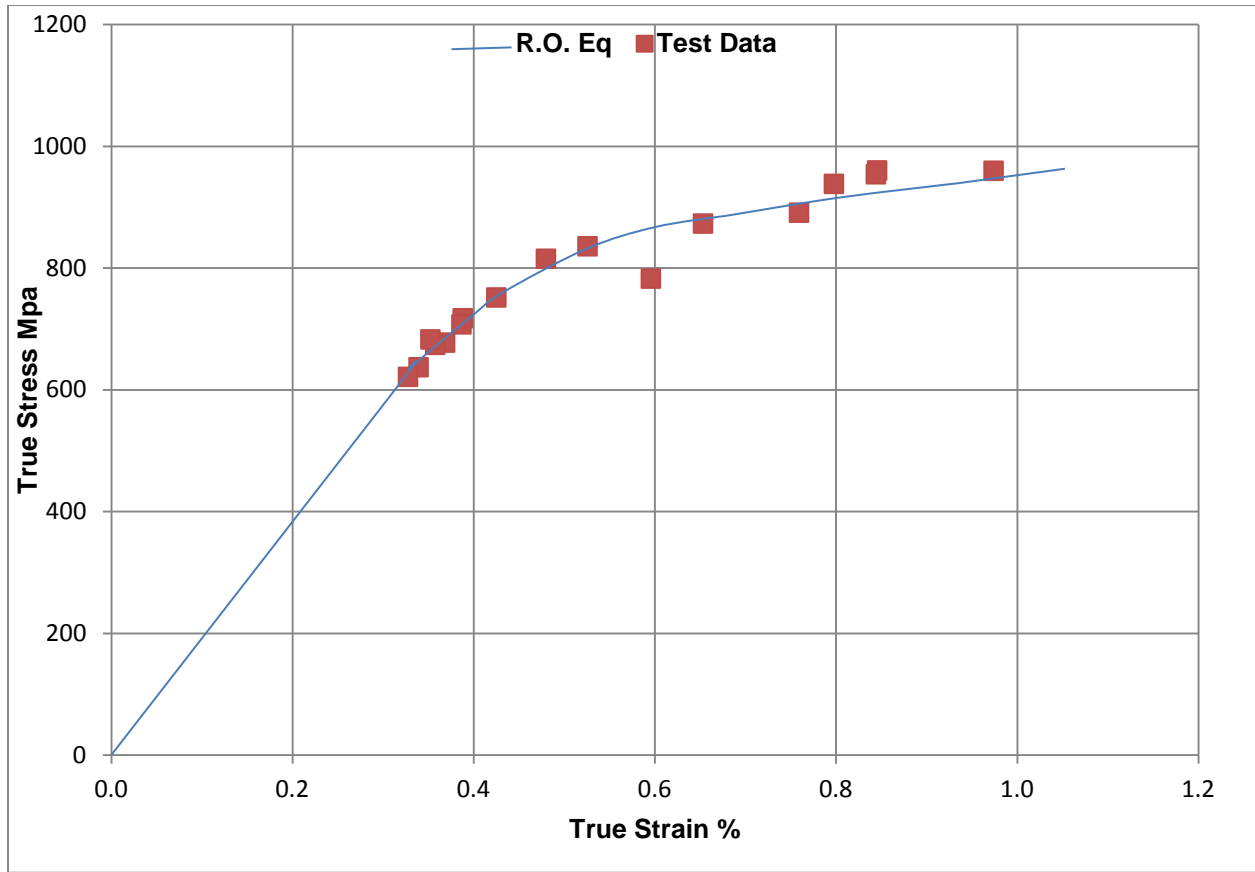


Figure 3: Cyclic true stress-strain curve for AISI 4320 (IT 124)

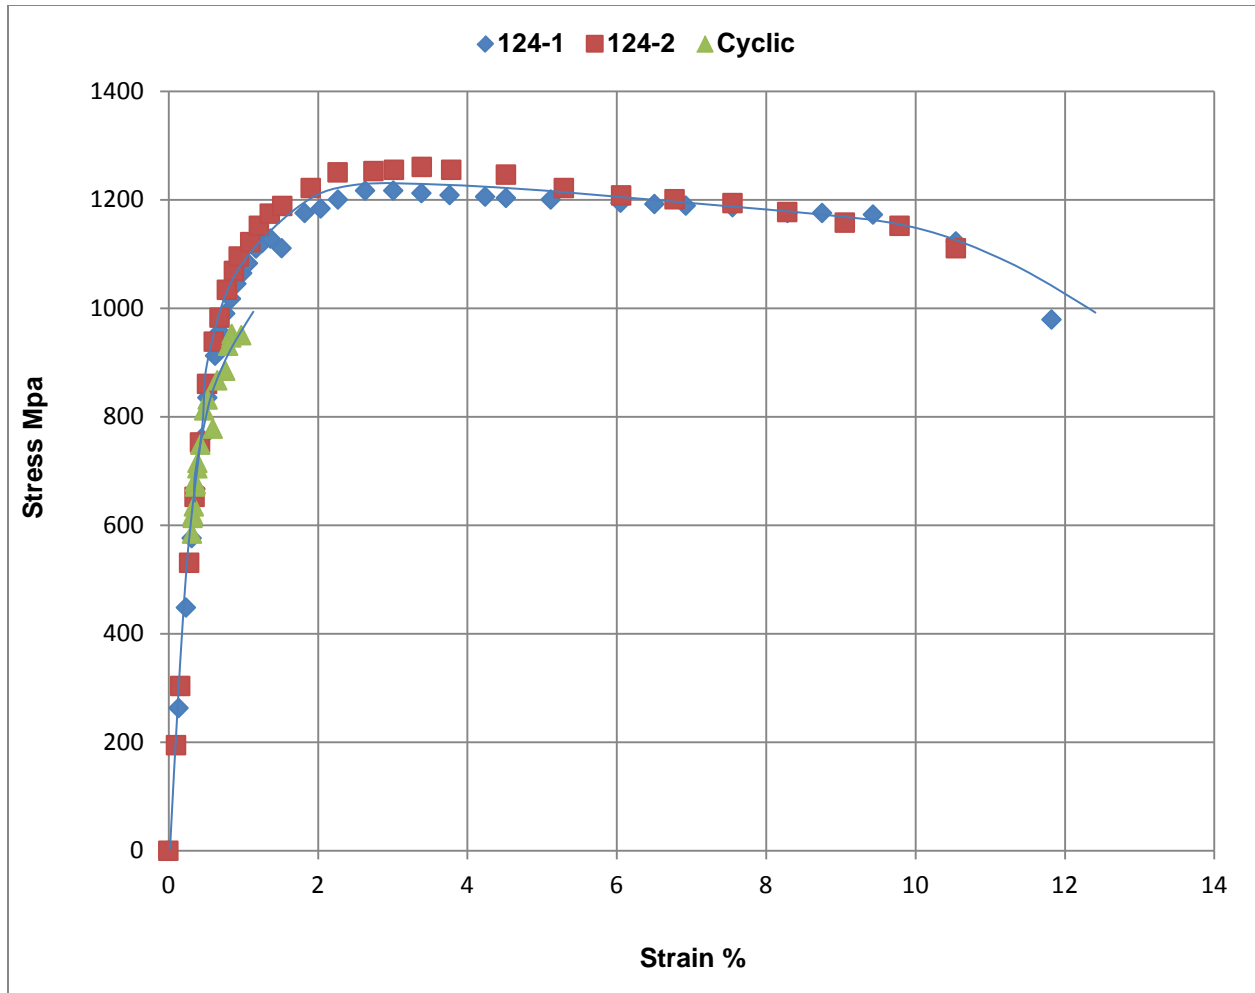


Figure 4: Monotonic & cyclic true stress-strain curves for AISI 4320 Steel (IT 124)

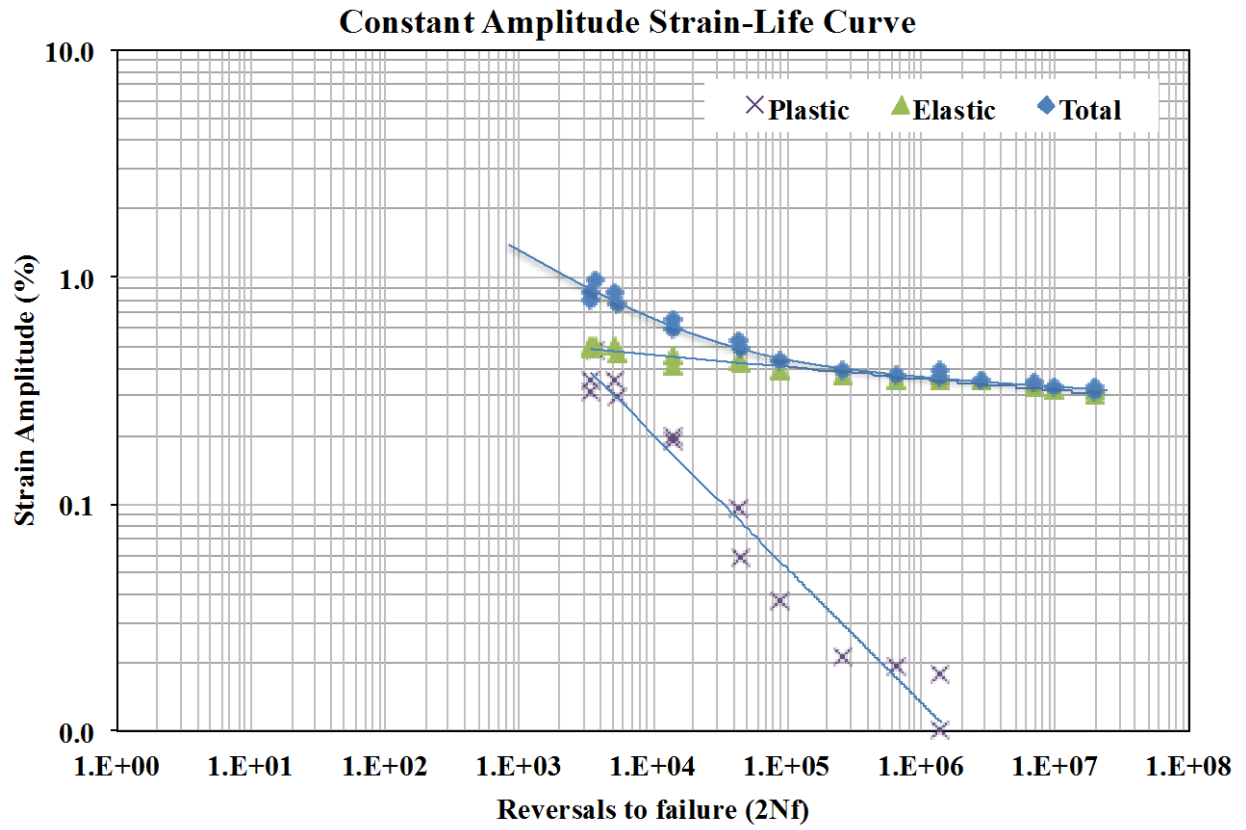


Figure 5: Strain-life fatigue curves for AISI 4320 (IT 124)

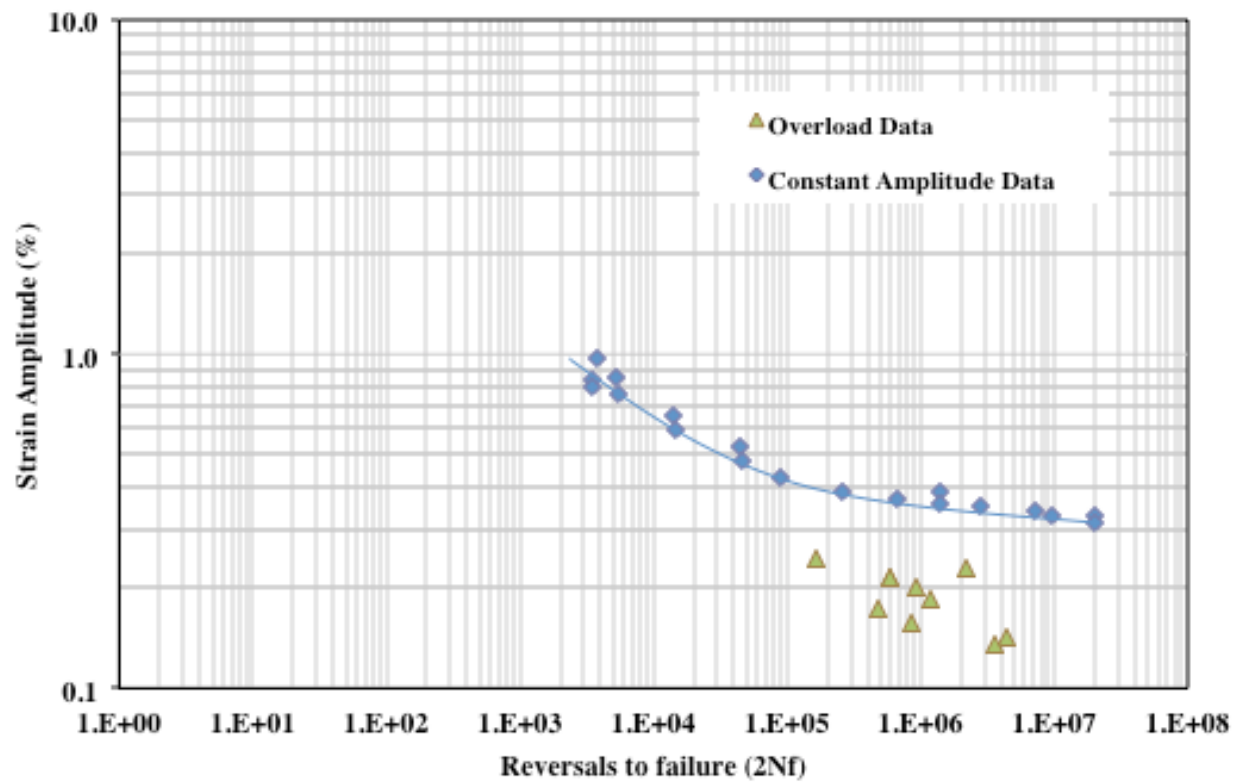


Figure 6: Overload and constant fatigue curves for AISI 4320 (IT 124)

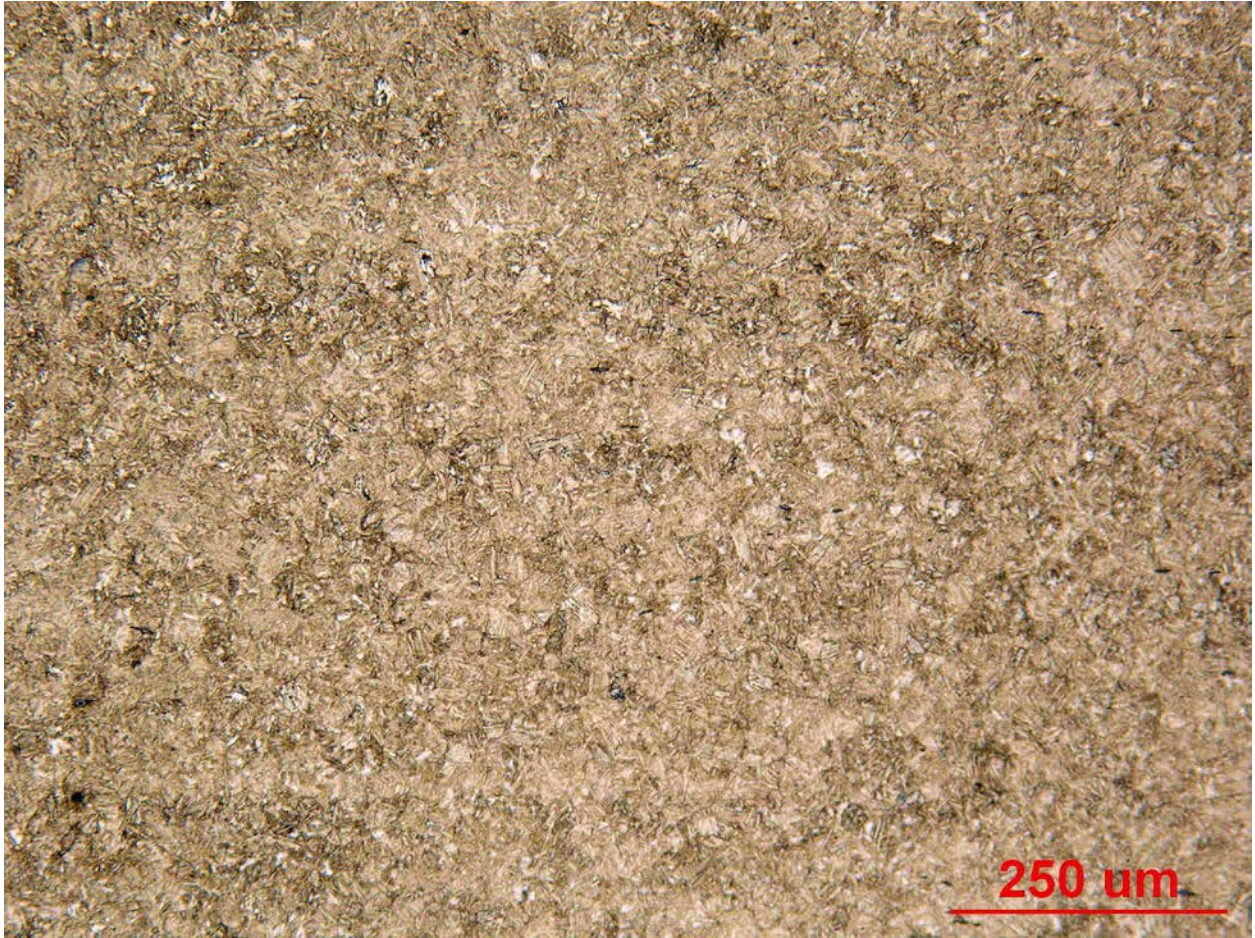


Figure 7: Microstructure of Iteration 124/148, low magnification

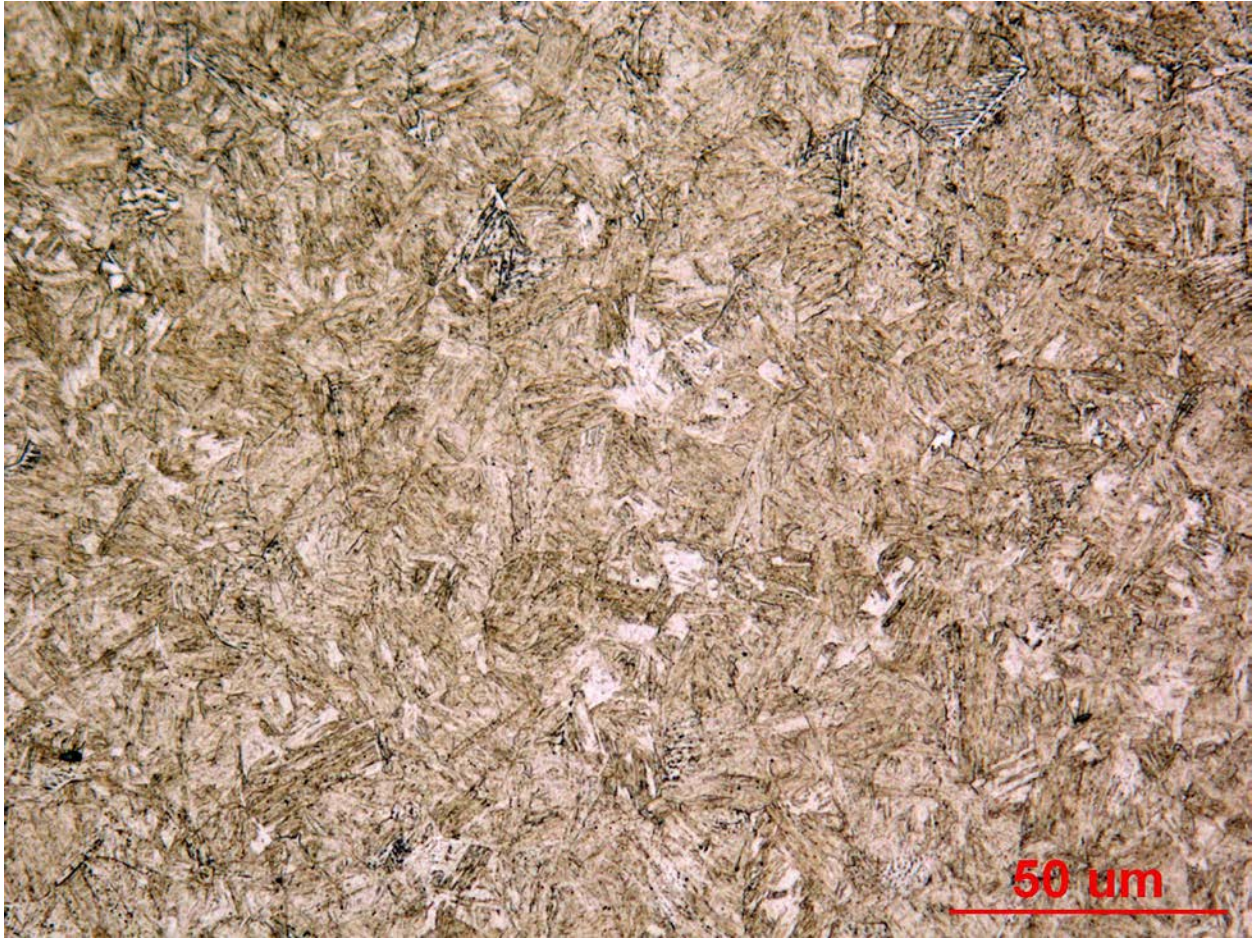


Figure 8: Microstructure of Iteration 124/148, high magnification

**Table 1: Chemical Analysis (Bar Average) for AISI 4320 Steel
(Iterations 124 and 148)**

C	0.19
Mn	0.62
P	0.007
S	0.025
Si	0.24
Ni	1.76
Cr	0.5
Mo	0.25
Cu	0.16
Sn	0.007
Al	0.02
V	0.004

**Table 2: Monotonic and Cyclic Properties for AISI 4320 Steel
(IT 124 and 148)**

<u>Monotonic Properties</u>	
Average elastic modulus, E (GPa)	193.6
Yield strength (MPa)	867
Ultimate tensile strength (MPa)	1238
% Elongation (%)	11%
% Reduction of area (%)	55.2%
True fracture strain, $Ln (A_i / A_f)$ (%)	80.4%
True fracture stress, $\sigma_f = \frac{P_f}{A_f}$ (MPa)	2336
Monotonic tensile strength coefficient, K (MPa)	1538
Monotonic tensile strain hardening exponent, n	0.067
Hardness, Rockwell C (HRC)	38.6
<u>Cyclic Properties</u>	
Cyclic Yield Strength, (0.2% offset) = $K'(0.002)^{n'}$ (MPa)	836
Cyclic strength coefficient, K' (MPa)	1572
Cyclic strain hardening exponent, n'	0.094
Cyclic elastic modulus, E _c (GPa)	193.6
Fatigue strength coefficient, σ_f' (MPa)	1547
Fatigue strength exponent, b	-0.057
Fatigue ductility coefficient, ϵ_f'	0.59
Fatigue ductility exponent, c	-0.61

Table 3: Constant Strain Amplitude Data for AISI 4320 Steel (IT 124)

Sp#	Total Strain	Stress Amplitude	Plastic Strain	Elastic Strain	(50% load drop)	Hardness
	Amplitude	(MPa)	Amplitude	Amplitude	Fatigue Life	(Rockwell HRc)
	(%)		(%)	(%)	(Reversals, 2Nf)	
11	0.974	960	0.475	0.495	3806	
12B	0.846	960	0.347	0.495	5188	
3B	0.844	954	0.349	0.492	3464	Hardness
20	0.798	938	0.311	0.484	3416	HRc
25	0.760	891	0.297	0.459	5434	Average
14	0.653	873	0.201	0.450	14280	of nine
24	0.596	783	0.191	0.403	14500	readings
10	0.526	836	0.094	0.431	44124	38.6
26	0.480	815	0.058	0.420	46282	
9	0.425	751	0.037	0.387	88200	
17	0.388	717	0.018	0.370	1375764	
18	0.387	708	0.021	0.365	259292	
5	0.369	678	0.019	0.349	669658	
16	0.358	674	0.010	0.347	1413586	
19	0.352	683	0.000	0.352	2796824	
6	0.339	637	0.011	0.328	7221420	
7	0.328	621	0.007	0.320	9730874	
12	0.326	615	0.008	0.317	20000000	
3	0.314	586	0.011	0.302	20000000	

Table 4: Overload Data for AISI 4320 Steel (IT 124)

SP#	Stress Amplitude for small cycles (MPa)	Strain Amplitude for small cycles (%)	Number of cycles between overloads	Total number of cycles to failure	Equivalent fatigue life	
					(Cycles-Nf)	(Reversals-2Nf)
4	410	0.214	400	276,791	296,656	593312
8	383	0.2	200	380,895	468,178	936356
13	356	0.186	200	459,084	592,923	1185846
21	329	0.172	300	221,118	237,940	475880
22	302	0.158	300	381,367	435,489	870978
23	275	0.143	350	1,342,575	2,172,218	4344436
27	262	0.136	1,000	1,506,941	1,772,766	3545532
28	410	0.214	100	229,775	295,385	590770
29	470	0.245	50	72,981	83,757	167514
30	438	0.228	50	346,328	1,104,818	2209636